

---


# Precision Crystal Calorimeters in High Energy Physics: Past, Present and Future

**Ren-Yuan Zhu**

California Institute of Technology





# Physics with Crystal Calorimeters




Charmonium system observed by CB through Inclusive photons

$H \rightarrow \gamma\gamma$  at LHC

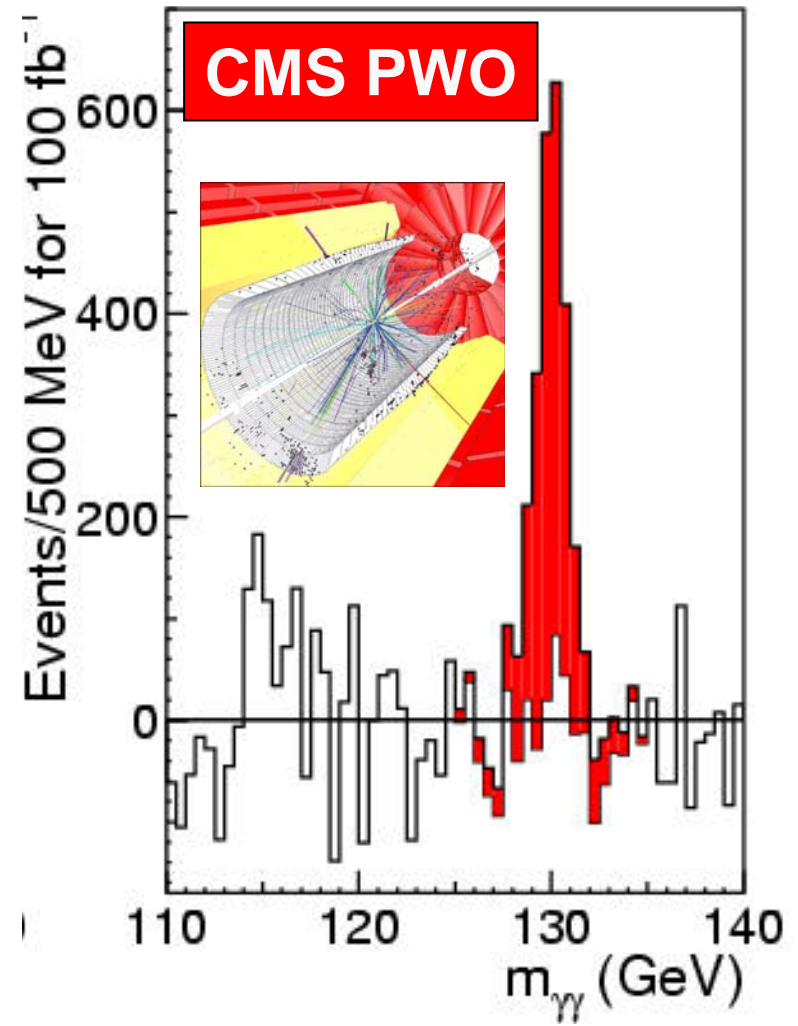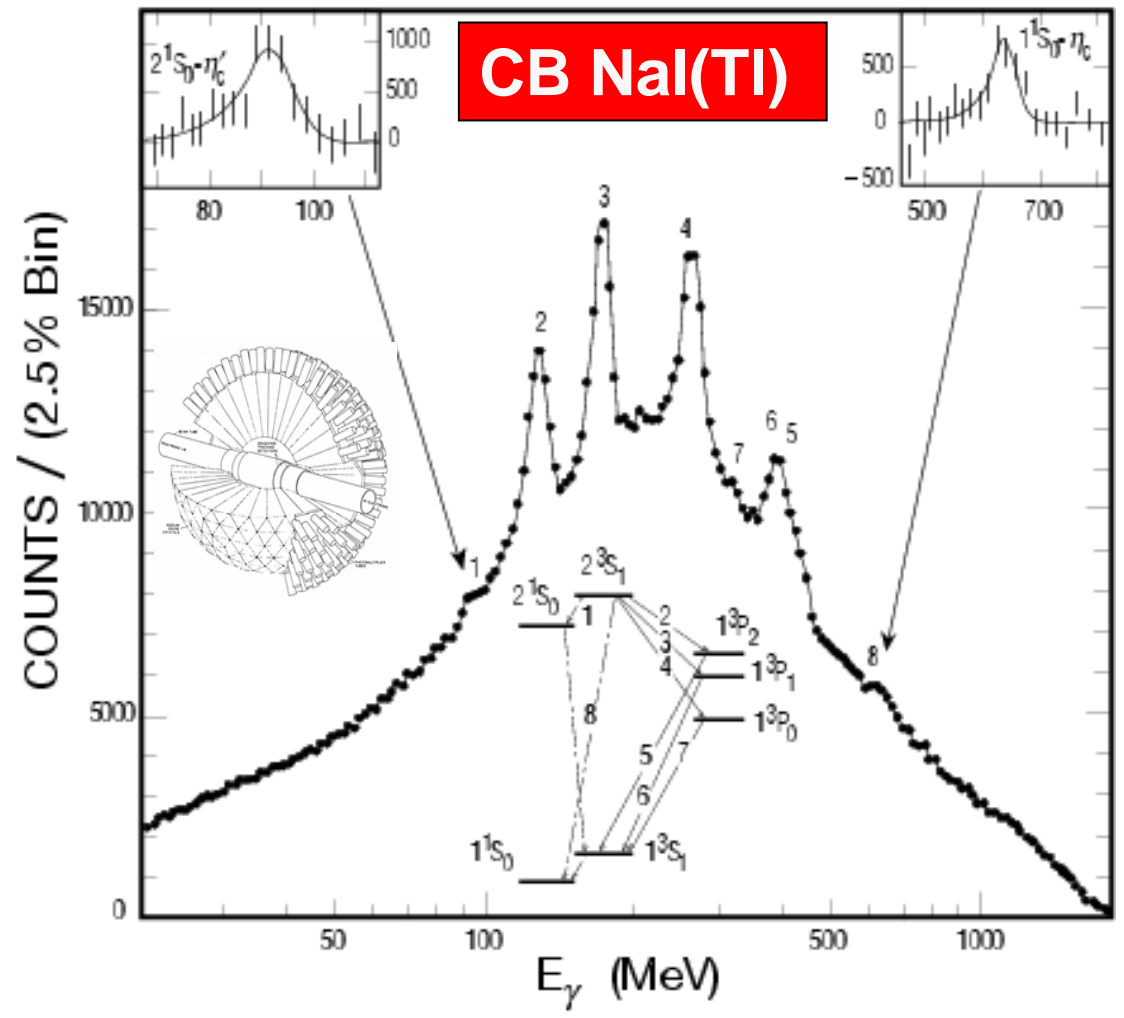



# Mass Produced Crystals





| Crystal                                     | Nal(Tl)         | CsI(Tl)                           | CsI        | BaF <sub>2</sub>      | BGO                   | PWO(Y)                           | LSO(Ce) | GSO(Ce) |
|---|-----------------|-----------------------------------|------------|-----------------------|-----------------------|----------------------------------|---------|---------|
| Density (g/cm <sup>3</sup> )                | 3.67            | 4.51                              | 4.51       | 4.89                  | 7.13                  | 8.3                              | 7.40    | 6.71    |
| Melting Point (°C)                          | 651             | 621                               | 621        | 1280                  | 1050                  | 1123                             | 2050    | 1950    |
| Radiation Length (cm)                       | 2.59            | 1.86                              | 1.86       | 2.03                  | 1.12                  | 0.89                             | 1.14    | 1.38    |
| Molière Radius (cm)                         | 4.13            | 3.57                              | 3.57       | 3.10                  | 2.23                  | 2.00                             | 2.07    | 2.23    |
| Interaction Length (cm)                     | 42.9            | 39.3                              | 39.3       | 30.7                  | 22.8                  | 20.7                             | 20.9    | 22.2    |
| Refractive Index <sup>a</sup>               | 1.85            | 1.79                              | 1.95       | 1.50                  | 2.15                  | 2.20                             | 1.82    | 1.85    |
| Hygroscopicity                              | Yes             | Slight                            | Slight     | No                    | No                    | No                               | No      | No      |
| Luminescence <sup>b</sup> (nm)<br>(at peak) | 410             | 550                               | 420<br>310 | 300<br>220            | 480                   | 425<br>420                       | 402     | 440     |
| Decay Time <sup>b</sup> (ns)                | 230             | 1250                              | 30<br>6    | 630<br>0.9            | 300                   | 30<br>6                          | 40      | 60      |
| Light Yield <sup>b,c</sup> (%)              | 100             | 165                               | 3.6<br>1.1 | 36<br>3.4             | 21                    | 0.29<br>.083                     | 83      | 30      |
| d(LY)/dT <sup>b</sup> (%/°C)                | ~0              | 0.3                               | -0.6       | -2<br>~0              | -1.6                  | -1.9                             | ~0      | -0.1    |
| Experiment                                  | Crystal<br>Ball | CLEO<br>BaBar<br>BELLE<br>BES III | KTeV       | TAPS<br>(L*)<br>(GEM) | L3<br>BELLE<br>PANDA? | CMS<br>ALICE<br>PrimEx<br>PANDA? | -       | -       |

a. at peak of emission; b. up/low row: slow/fast component; c. PMT QE taken out.




# Crystal Density: Radiation Length

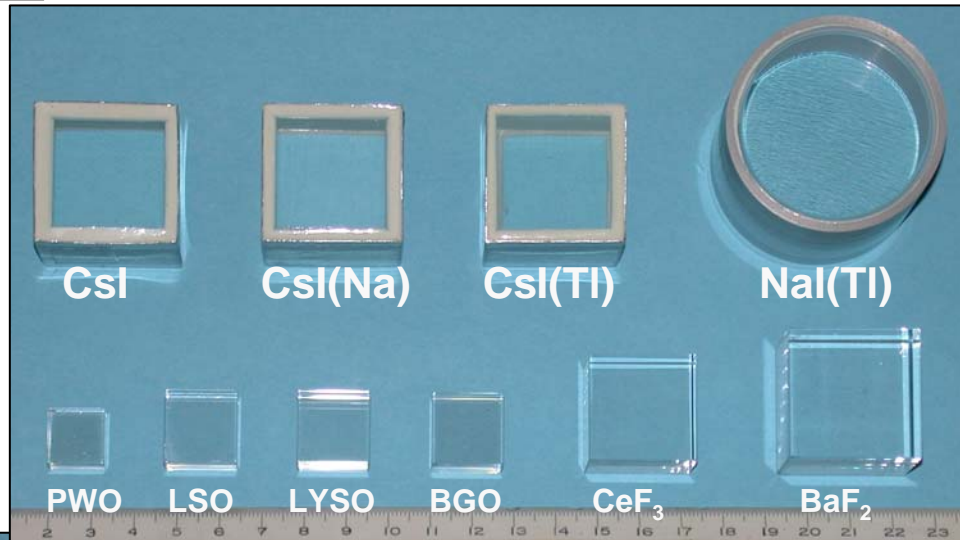

1.5  $X_0$  Samples:

Hygroscopic Halides

Non-hygroscopic

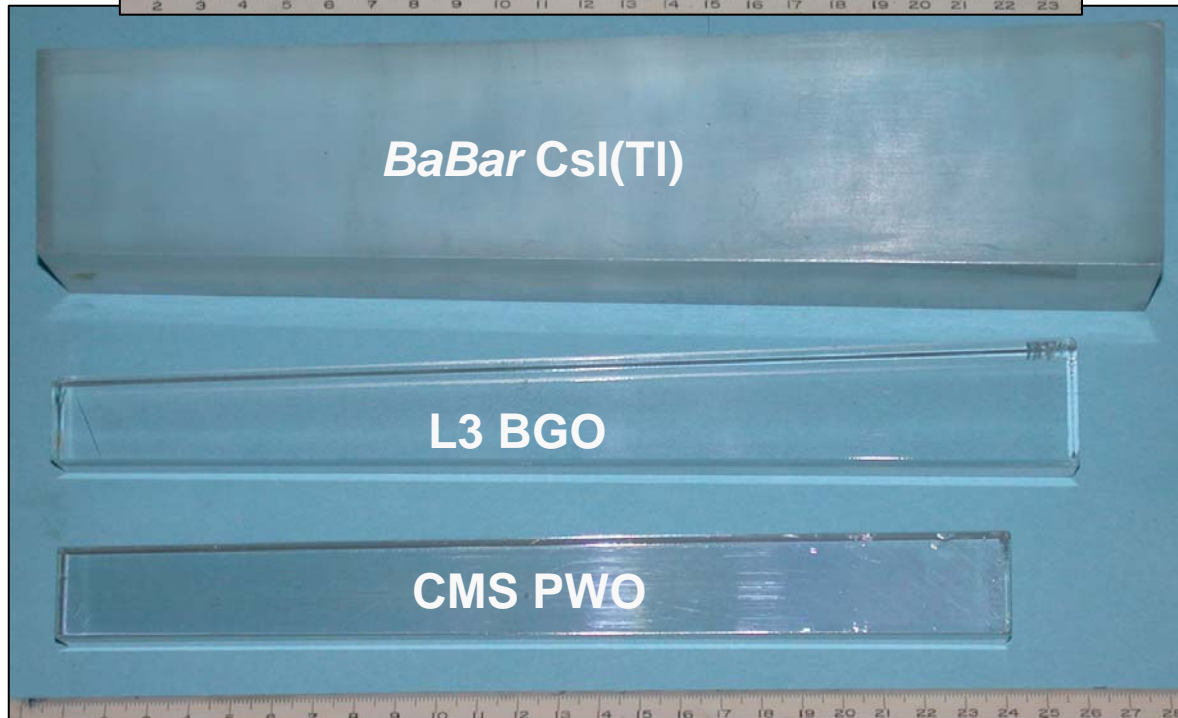

Full Size Crystals:


*BaBar* Csl(Tl): 16  $X_0$

L3 BGO: 22  $X_0$

CMS PWO(Y): 25  $X_0$




# Excitation, Emission & Transmission



$$T_s = (1 - R)^2 + R^2(1 - R)^2 + \dots = (1 - R)/(1 + R), \text{ with}$$


$$R = \frac{(n_{crystal} - n_{air})^2}{(n_{crystal} + n_{air})^2}.$$

Theoretical limit of transmittance: NIM A333 (1993) 422

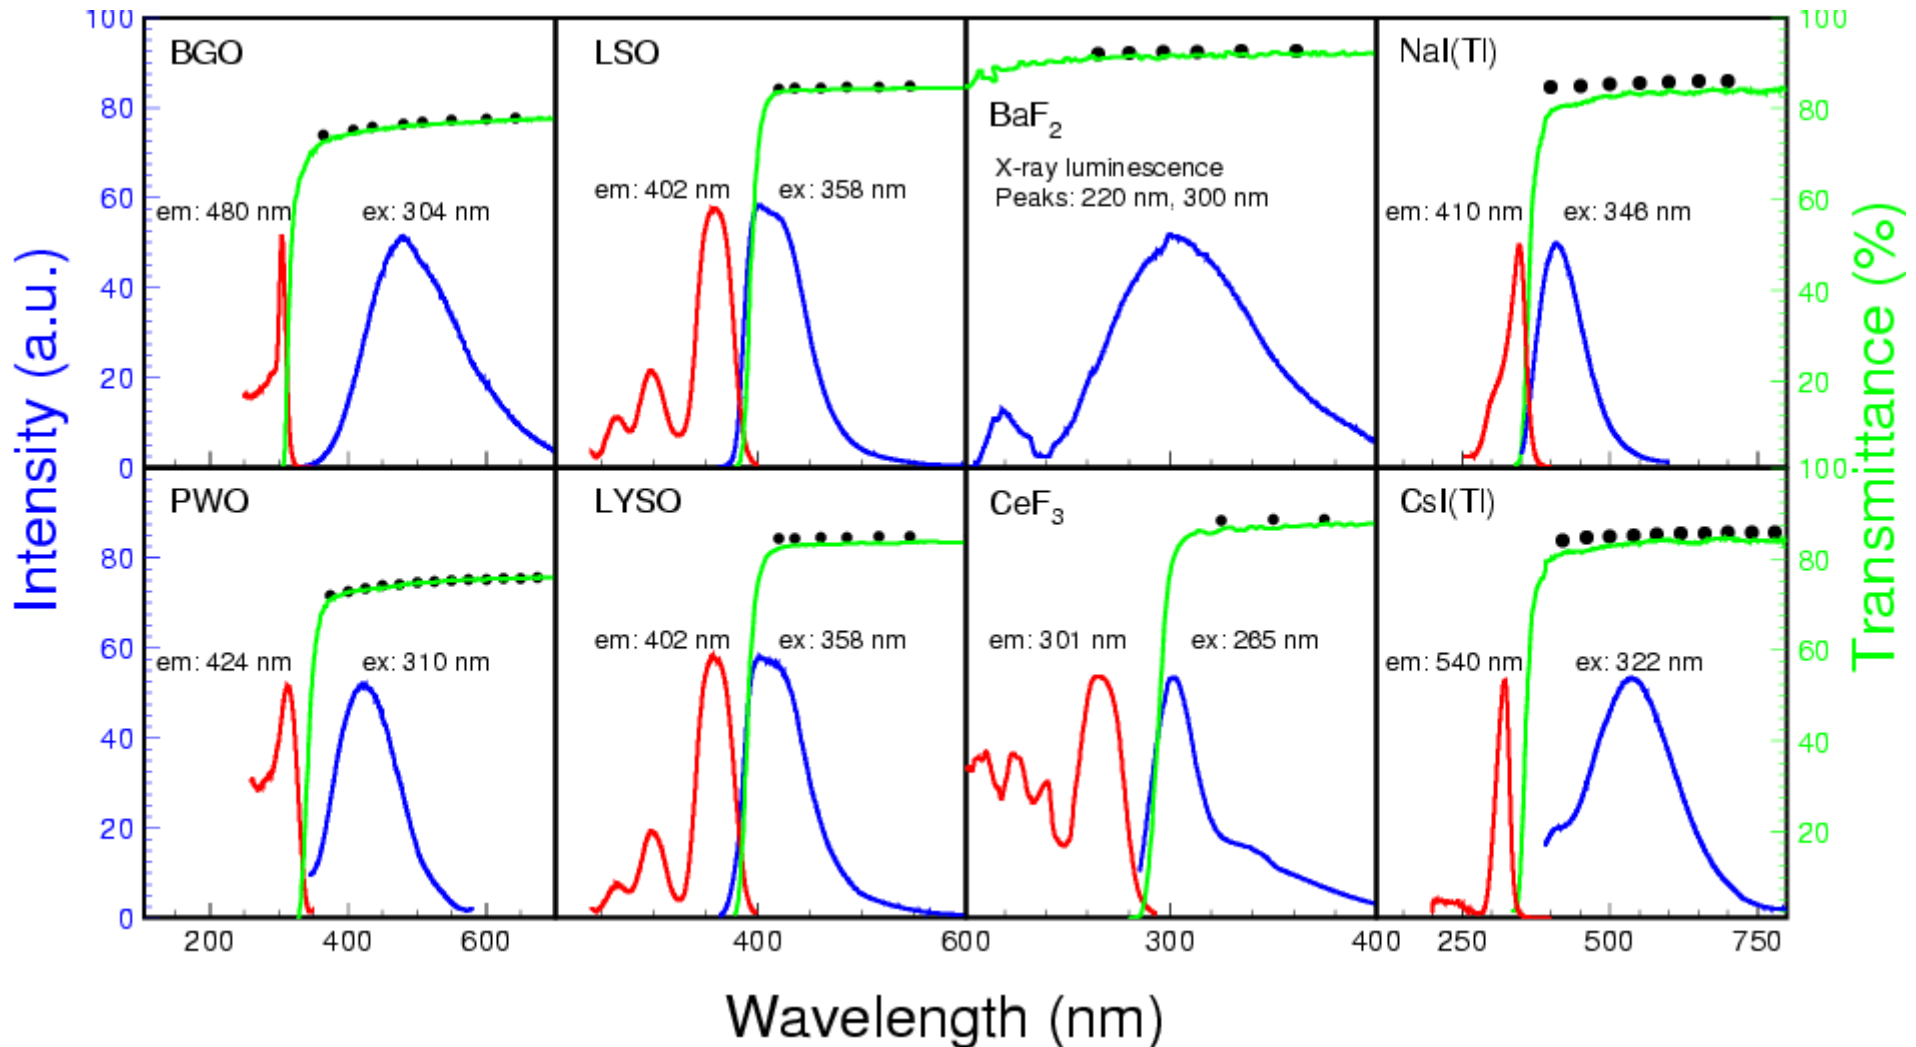





# Scintillation Light Decay Time



Recorded with an Agilent 6052A digital scope


## Fast Scintillators

## Slow Scintillators

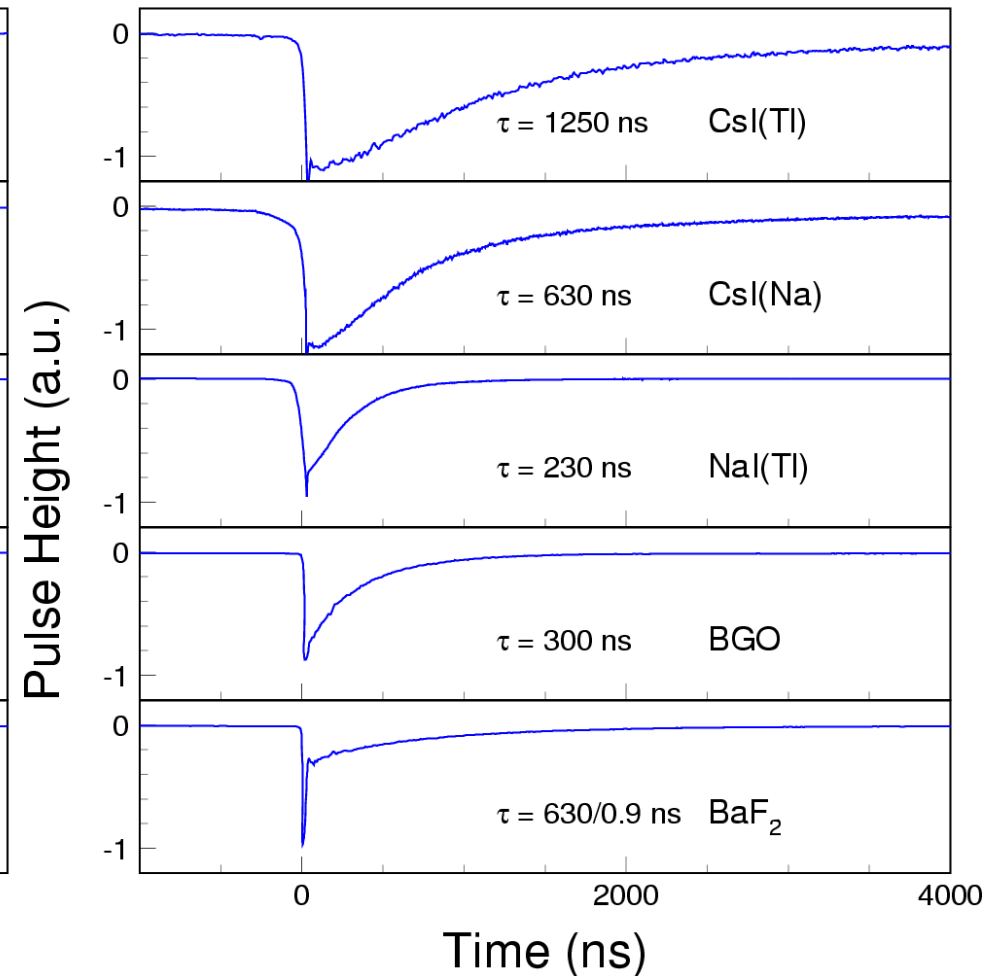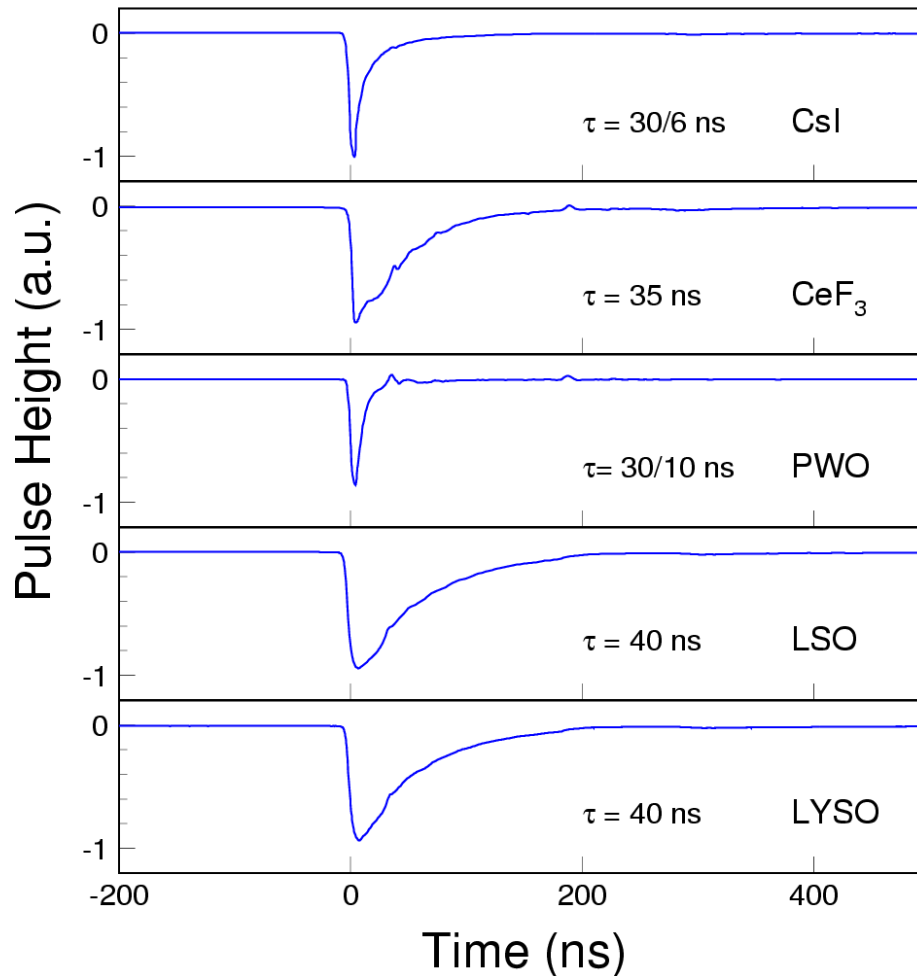




# Scintillation Light Output




Measured with a Philips XP2254B PMT (multi-alkali cathode)  
 p.e./MeV: LSO/LYSO is 6 & 230 times of BGO & PWO respectively

## Fast Scintillators

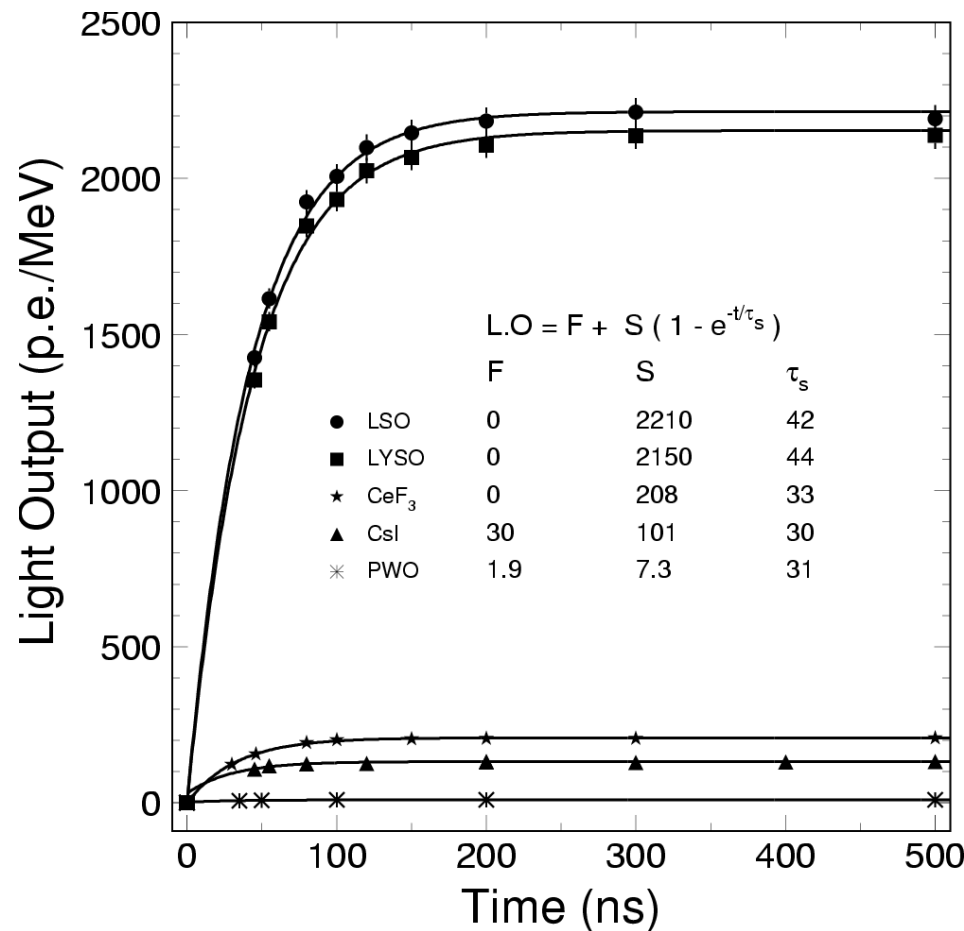


## Slow Scintillators


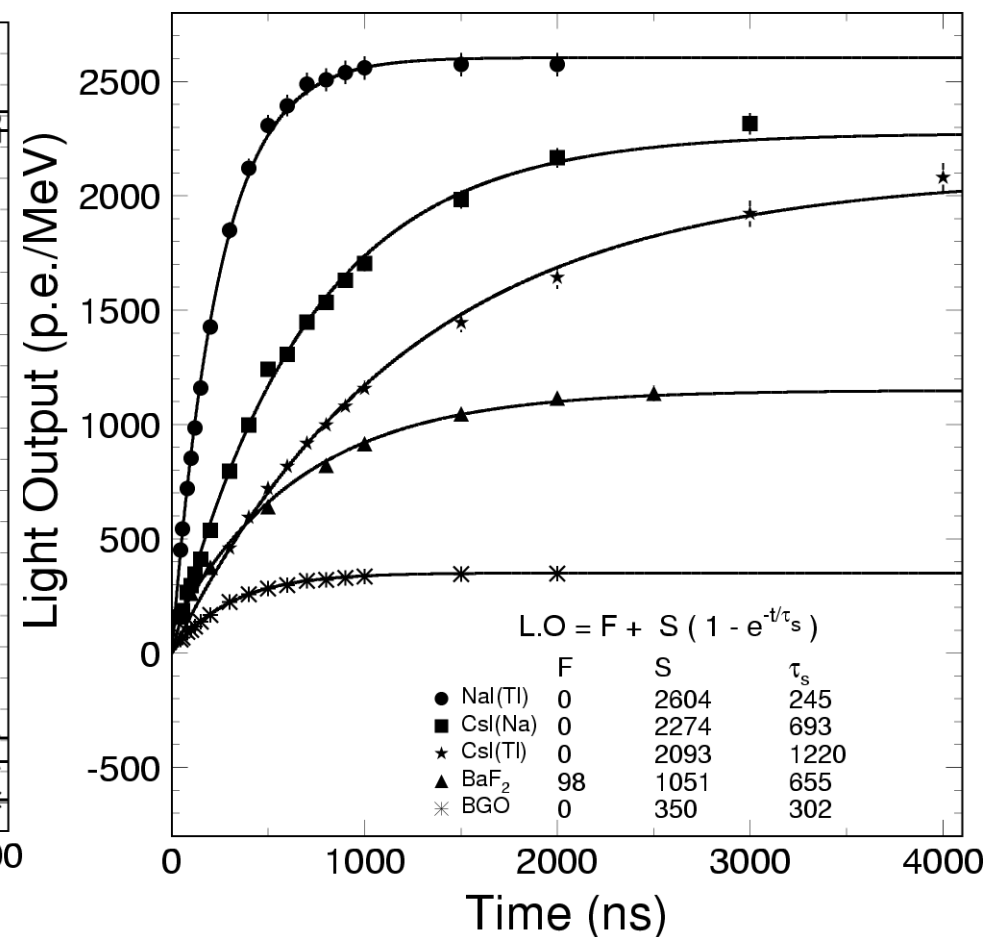




# Emission Weighted PMT Q.E.




Taking out QE, L.O. of LSO/LYSO is 4/200 times BGO/PWO  
Hamamatsu S8664-55 APD has QE 75% for LSO/LYSO

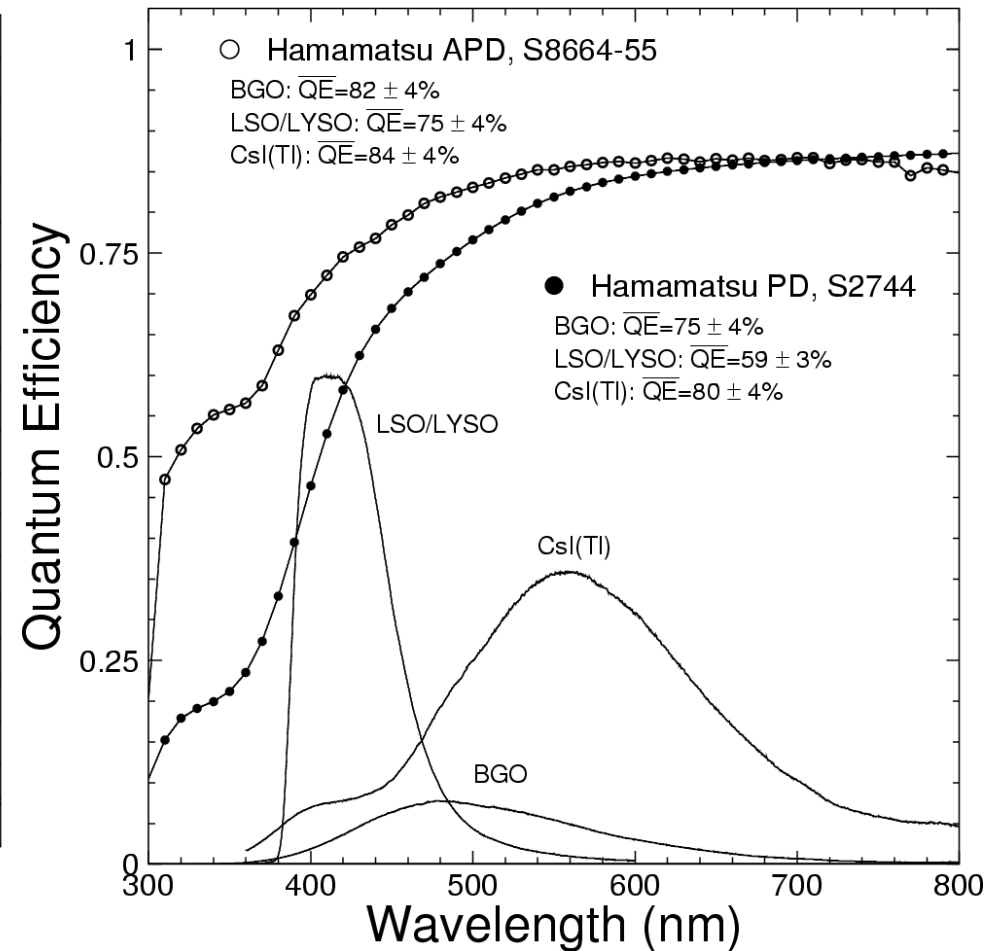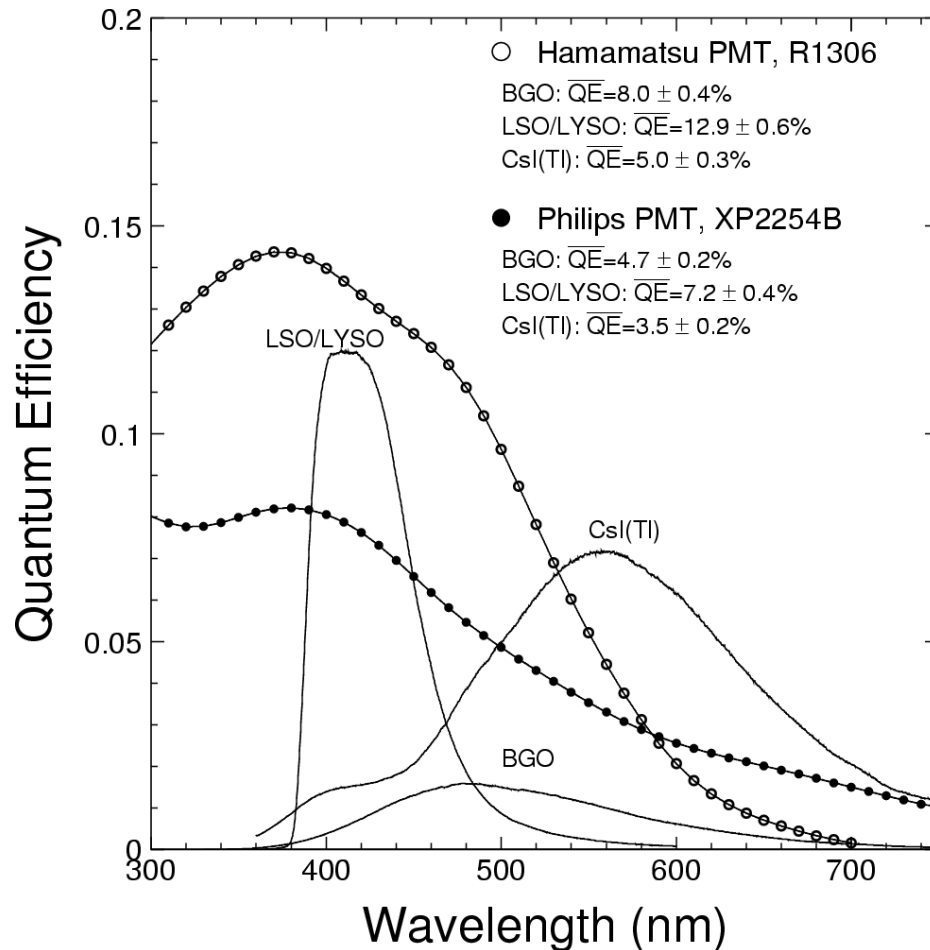






# BGO, LSO & LYSO Samples




2.5 x 2.5 x 20 cm (18 X<sub>0</sub>)


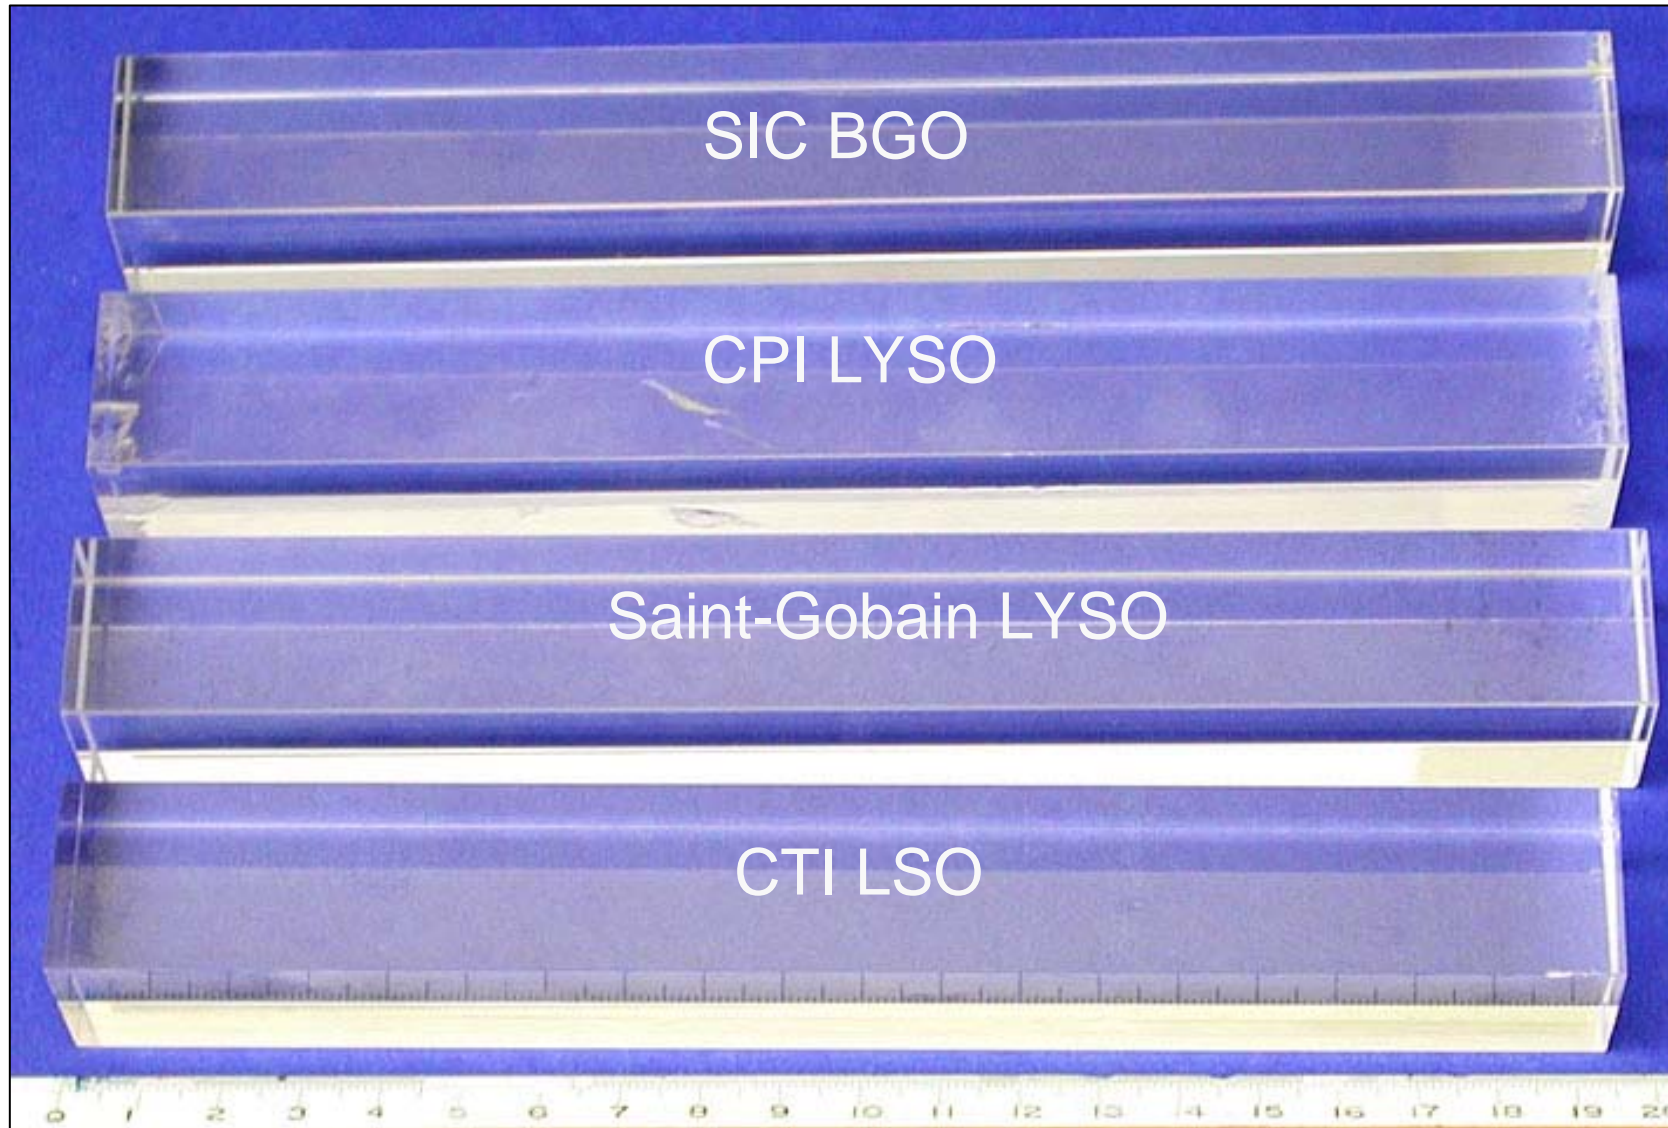




# LSO/LYSO with PMT Readout




~10% FWHM resolution for  $^{22}\text{Na}$  source (0.51 MeV)  
1,200 p.e./MeV, 5/230 times of BGO/PWO

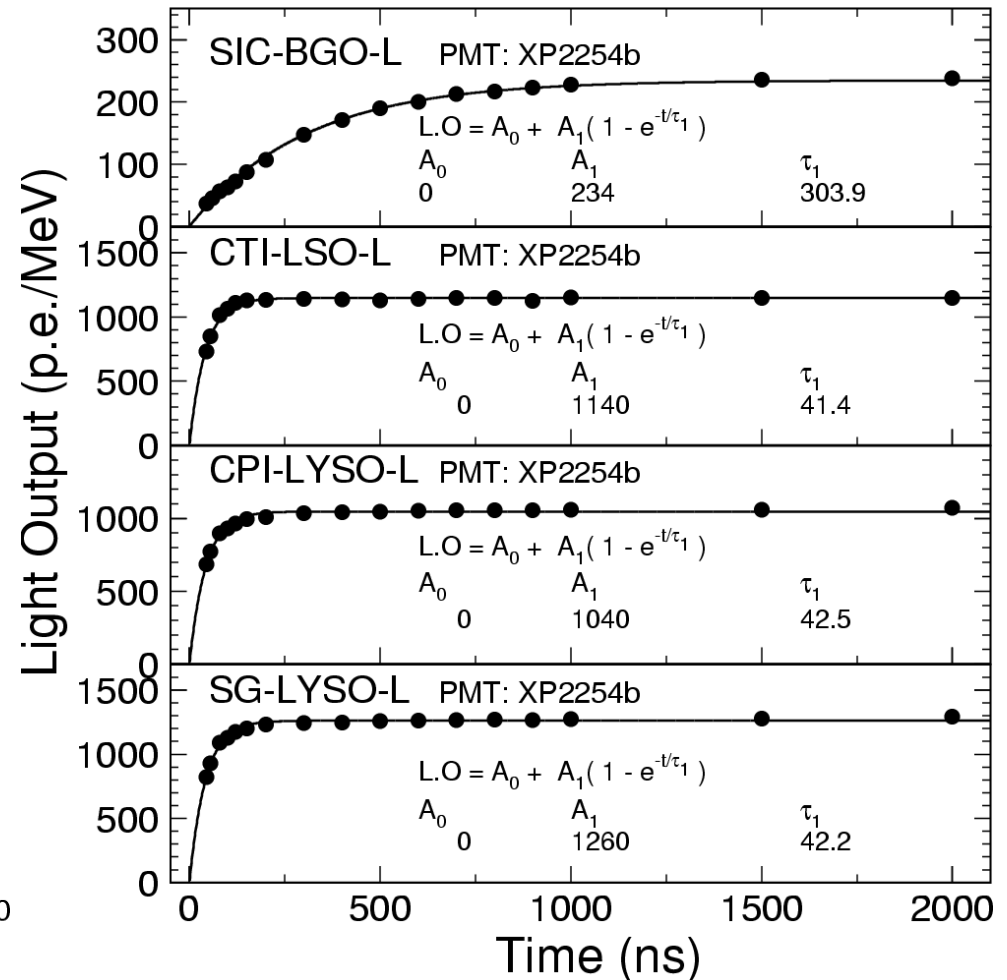
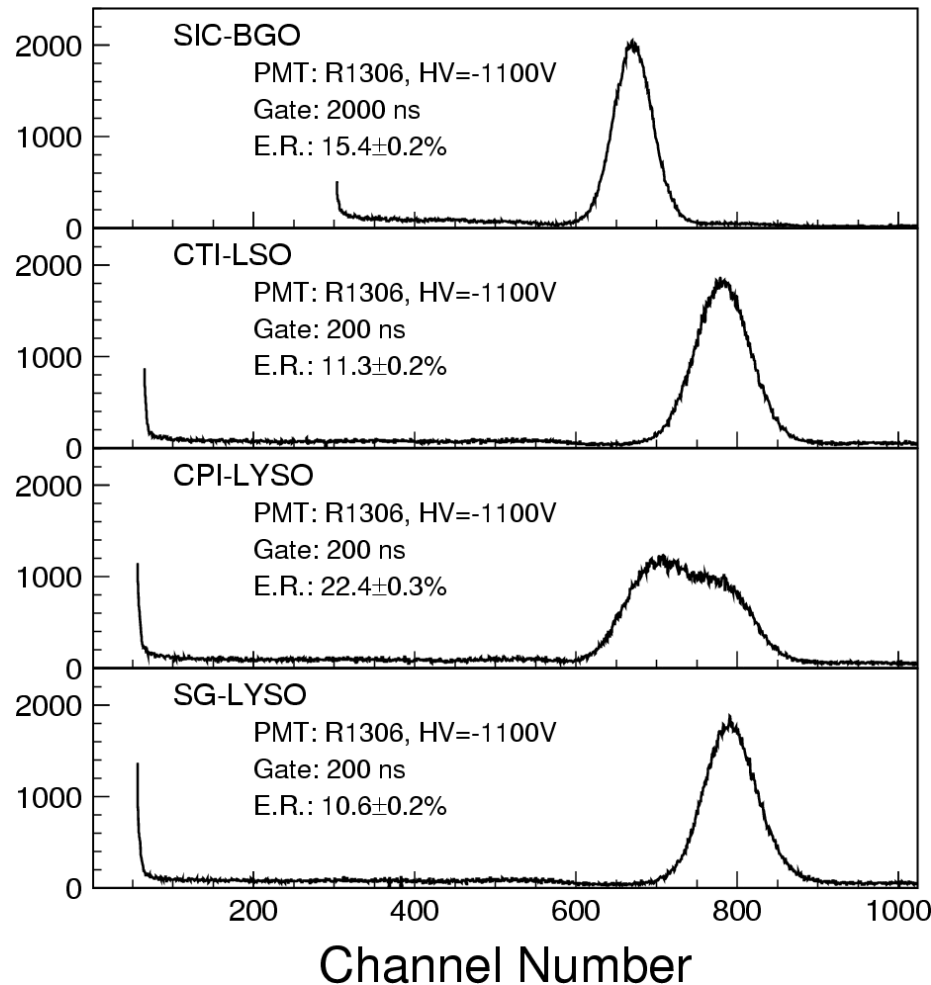




# LSO/LYSO with APD Readout




L.O.: 1,500 p.e./MeV, 4/200 times of BGO/PWO  
Readout Noise: <40 keV

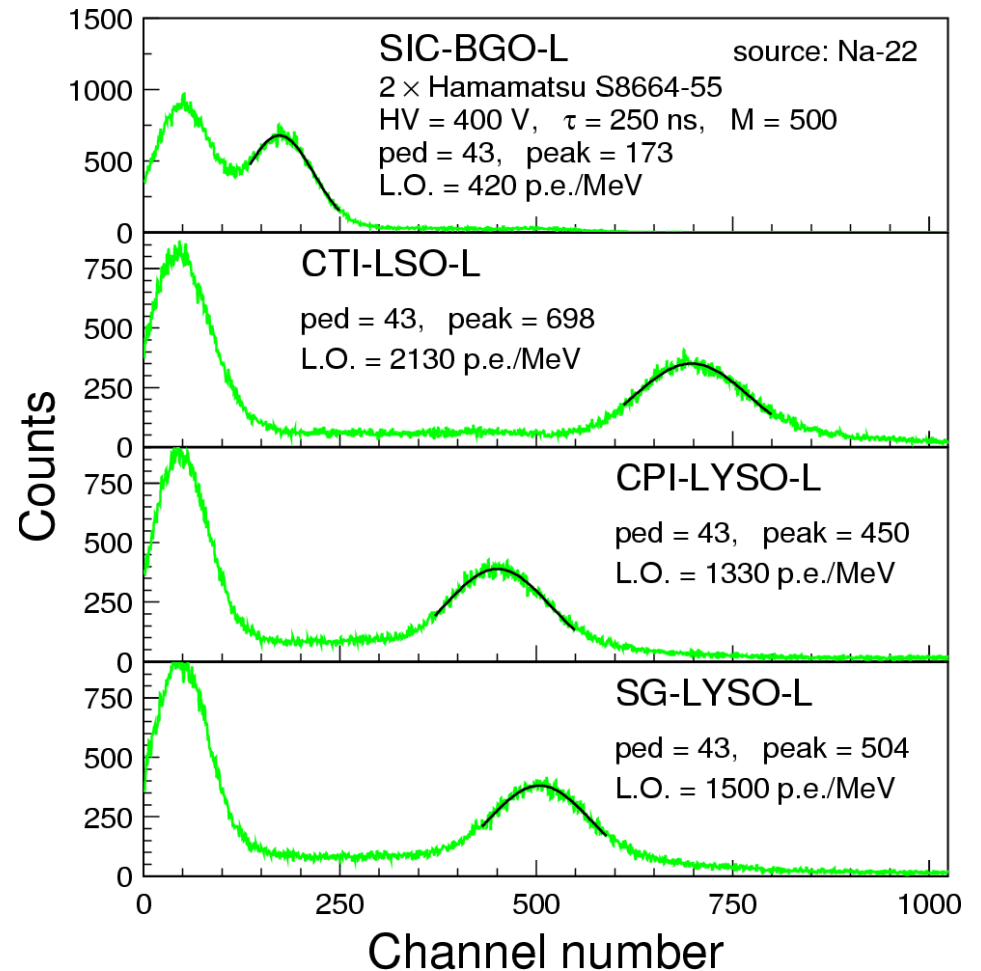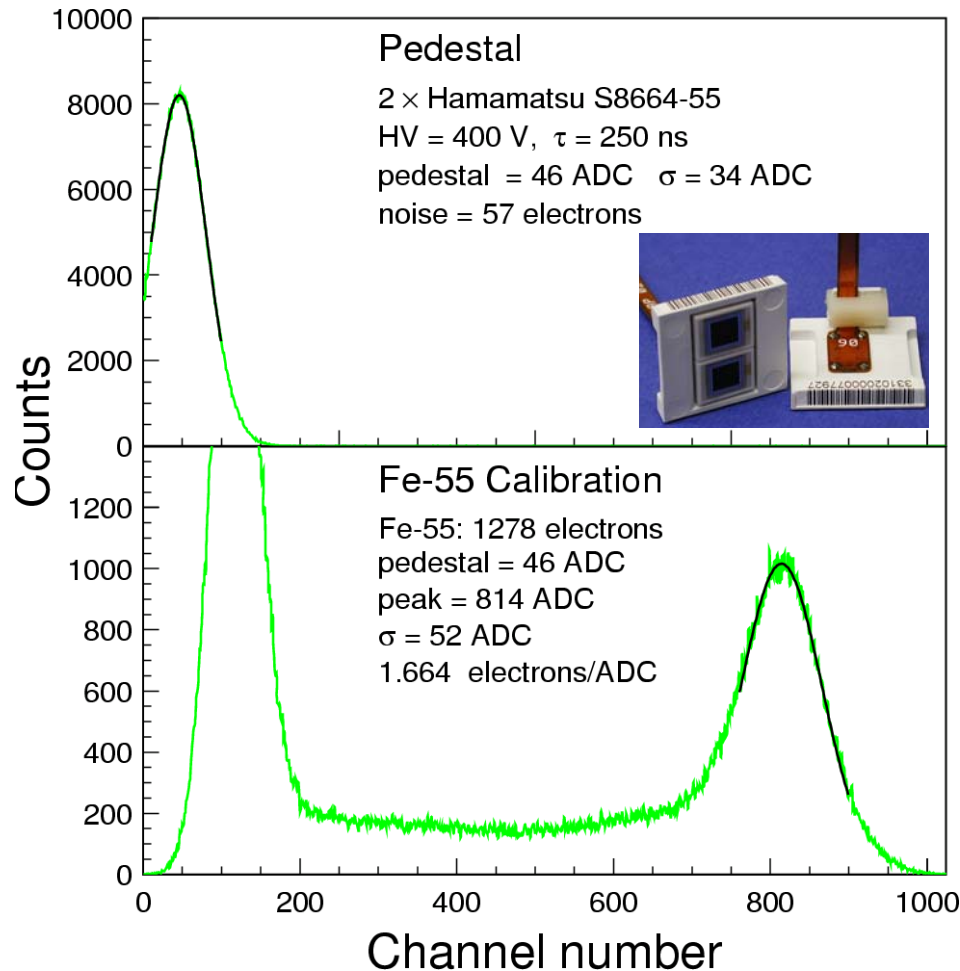



# Crystal Calorimeters in HEP




| Date                             | 75-85           | 80-00           | 80-00           | 80-00                  | 90-10           | 94-10           | 94-10           | 95-20             |
|----------------------------------|-----------------|-----------------|-----------------|------------------------|-----------------|-----------------|-----------------|-------------------|
| Experiment                       | C. Ball         | L3              | CLEO II         | C. Barrel              | KTeV            | <i>BaBar</i>    | BELLE           | CMS               |
| Accelerator                      | SPEAR           | LEP             | CESR            | LEAR                   | FNAL            | SLAC            | KEK             | CERN              |
| Crystal Type                     | NaI(Tl)         | BGO             | CsI(Tl)         | CsI(Tl)                | CsI             | CsI(Tl)         | CsI(Tl)         | PbWO <sub>4</sub> |
| B-Field (T)                      | -               | 0.5             | 1.5             | 1.5                    | -               | 1.5             | 1.0             | 4.0               |
| $r_{inner}$ (m)                  | 0.254           | 0.55            | 1.0             | 0.27                   | -               | 1.0             | 1.25            | 1.29              |
| Number of Crystals               | 672             | 11,400          | 7,800           | 1,400                  | 3,300           | 6,580           | 8,800           | 76,000            |
| Crystal Depth ( $X_0$ )          | 16              | 22              | 16              | 16                     | 27              | 16 to 17.5      | 16.2            | 25                |
| Crystal Volume (m <sup>3</sup> ) | 1               | 1.5             | 7               | 1                      | 2               | 5.9             | 9.5             | 11                |
| Light Output (p.e./MeV)          | 350             | 1,400           | 5,000           | 2,000                  | 40              | 5,000           | 5,000           | 2                 |
| Photosensor                      | PMT             | Si PD           | Si PD           | WS <sup>a</sup> +Si PD | PMT             | Si PD           | Si PD           | APD <sup>a</sup>  |
| Gain of Photosensor              | Large           | 1               | 1               | 1                      | 4,000           | 1               | 1               | 50                |
| $\sigma_N$ /Channel (MeV)        | 0.05            | 0.8             | 0.5             | 0.2                    | small           | 0.15            | 0.2             | 40                |
| Dynamic Range                    | 10 <sup>4</sup> | 10 <sup>5</sup> | 10 <sup>4</sup> | 10 <sup>4</sup>        | 10 <sup>4</sup> | 10 <sup>4</sup> | 10 <sup>4</sup> | 10 <sup>5</sup>   |



**Future crystal calorimeters in HEP:**  
**PANDA at GSI: PWO or BGO?**  
**LSO/LYSO for a Super B Factory or ILC?**



# L3 BGO Resolution






| Contribution | “Radiative”+Intrinsic | Temperature | Calibration | Overall |
|--------------|-----------------------|-------------|-------------|---------|
| Barrel       | 0.8%                  | 0.5%        | 0.5%        | 1.07%   |
| Endcaps      | 0.6%                  | 0.5%        | 0.4%        | 0.88%   |

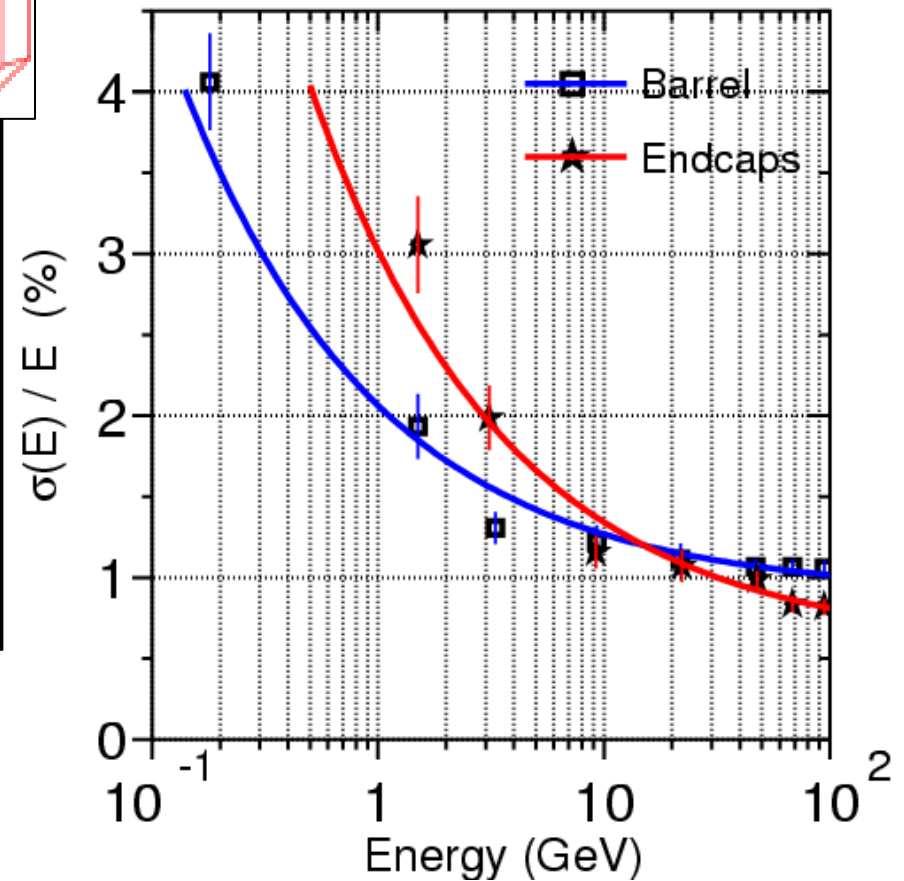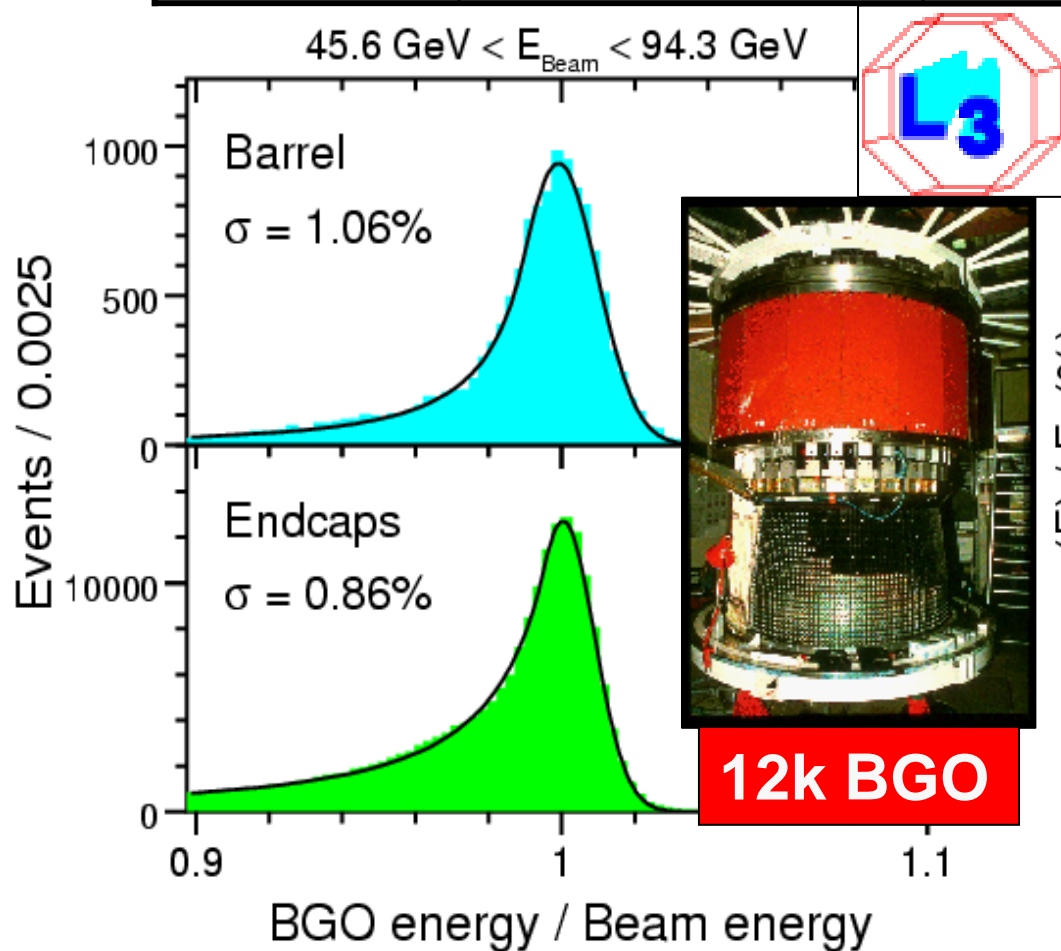




# KTeV CsI Position Resolution

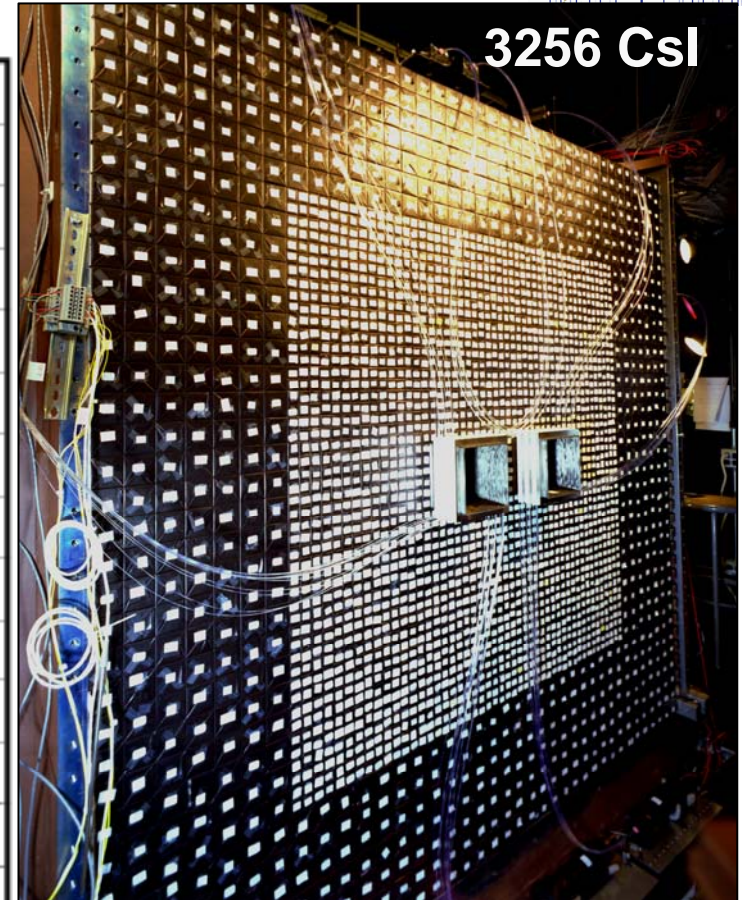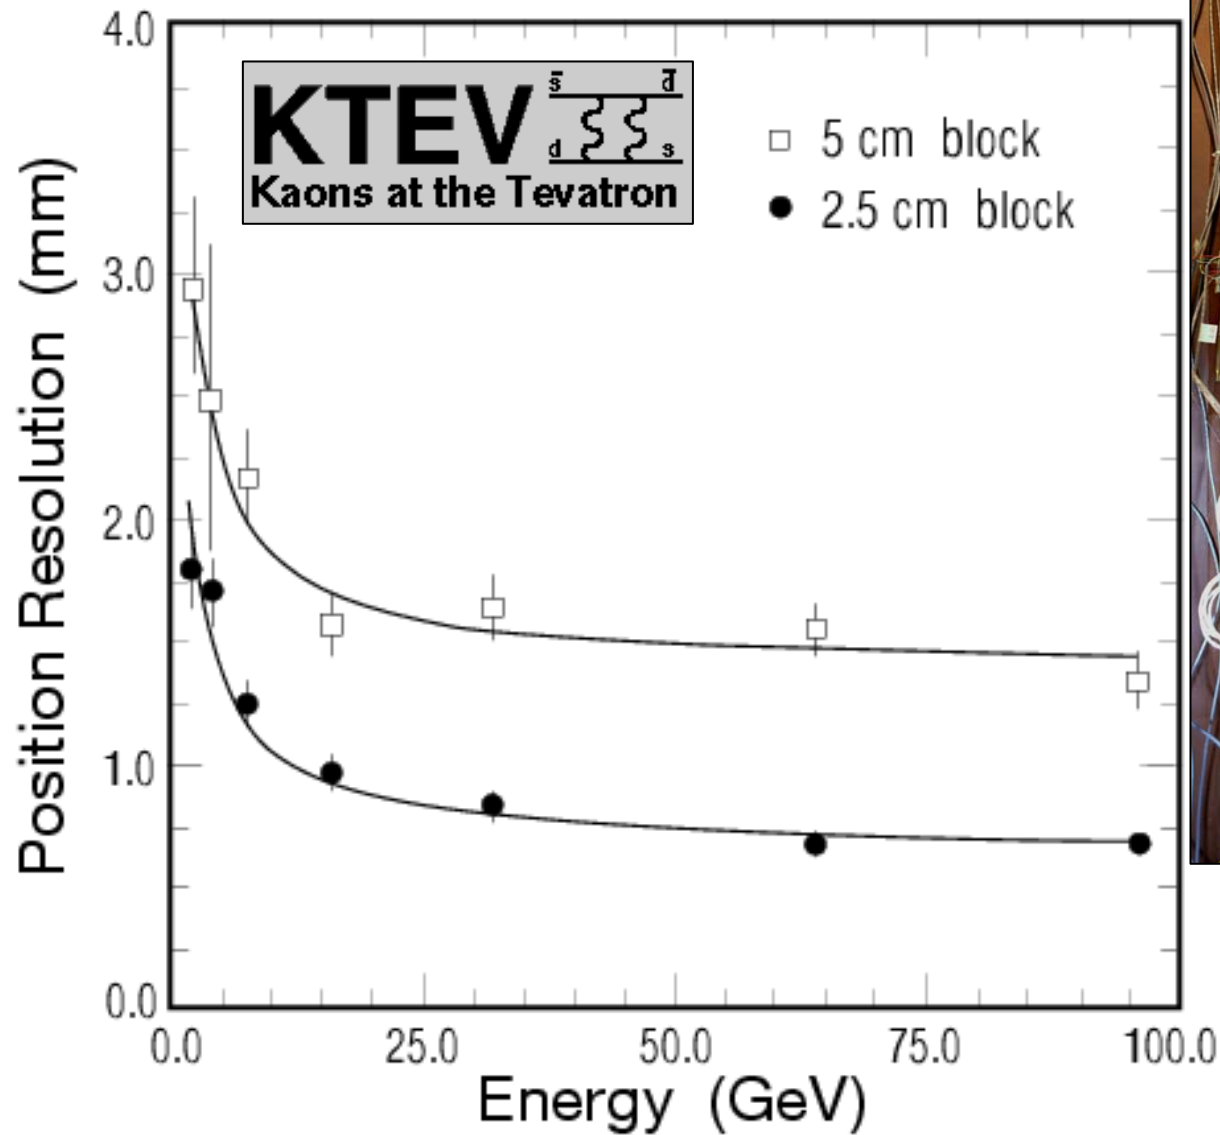


Sub mm position resolution.  
L3 BGO & CMS  
PWO: 0.3 mm.



# PWO Crystal ECAL Resolution



**PWO Crystal Radiation Damage?**  
See talks by Paramatti, Mao, Adi & Daskalakis


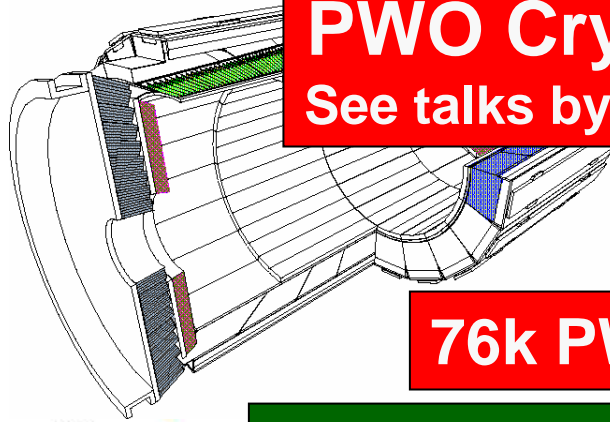


**76k PWO**



**Measured Resolution**  
 $\sigma(E)/E < 1\%$  if  $E > 25$  GeV  
 $\sigma(E)/E \sim 0.5\%$  at 120 GeV


**Designed Resolution**

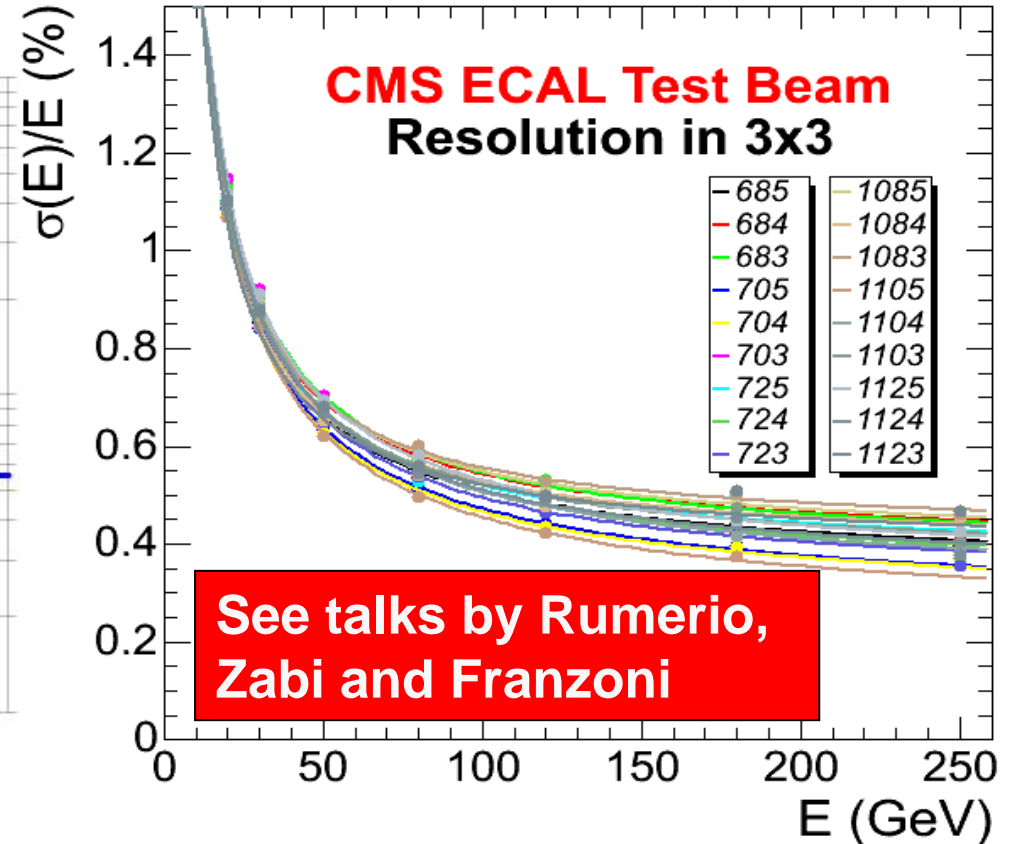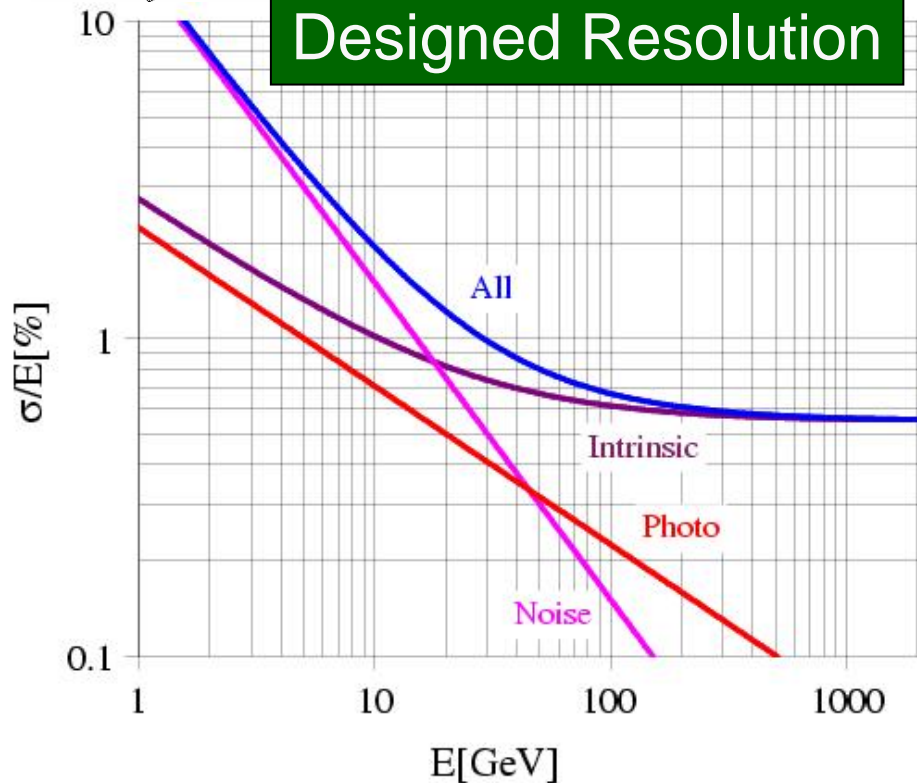

**See talks by Rumerio, Zabi and Franzoni**





# Crystal Degradation *in situ*



L3 BGO degrades 6 – 7% in 7 years


*BaBar* CsI(Tl): 1 - 3 % per year

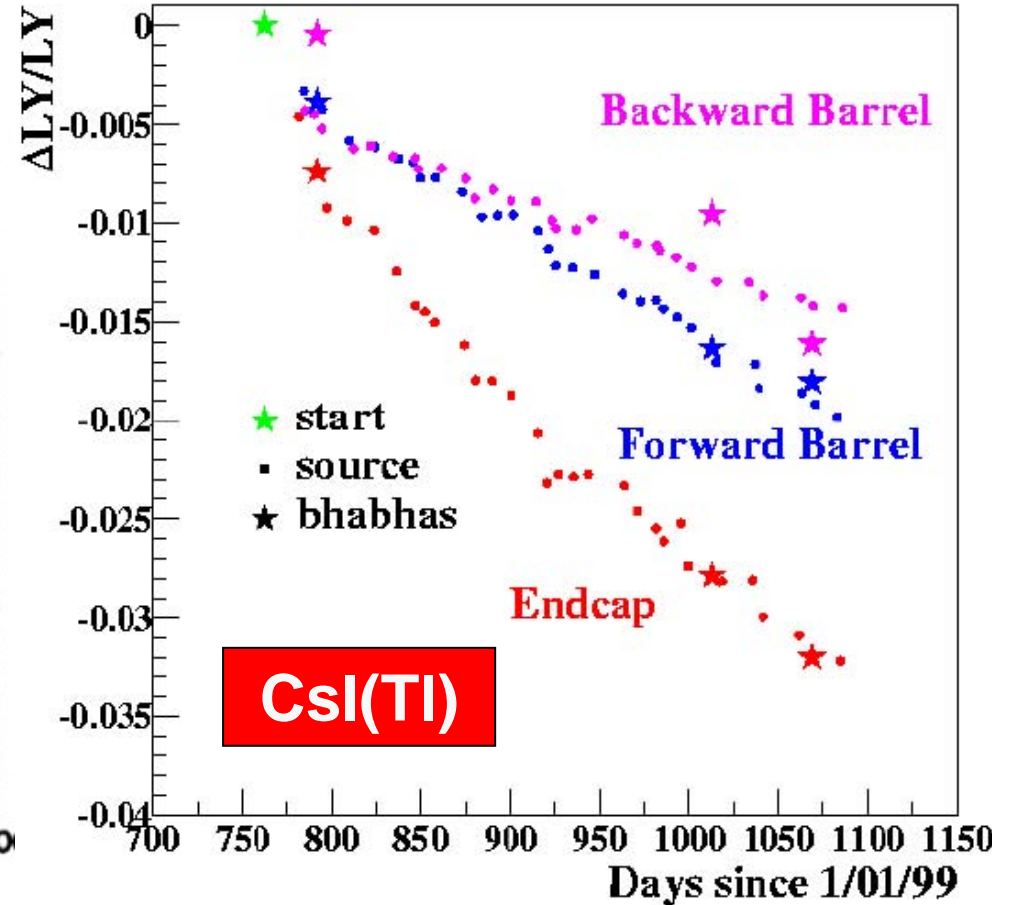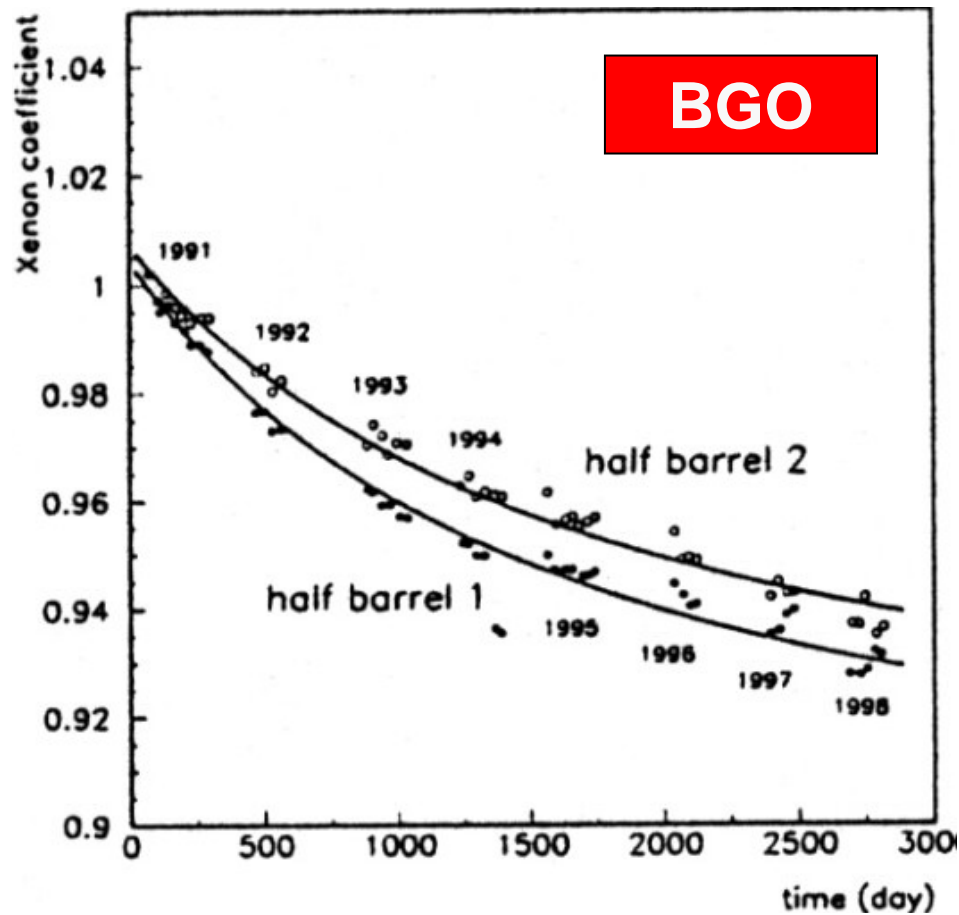





# Effects of Radiation Damage




- Induced absorption caused by color center formation:
  - reduced light attenuation length and thus light output, and maybe
  - degraded of light response uniformity (LRU).
- Induced phosphorescence:
  - increase readout noise.
- Reduced scintillation light yield:
  - reduce light output and degrade light response uniformity.



| Item                        | CsI(Tl) | CsI    | BaF <sub>2</sub> | BGO | PbWO <sub>4</sub> |
|-----------------------------|---------|--------|------------------|-----|-------------------|
| Color Centers               | Yes     | Yes    | Yes              | Yes | Yes               |
| Fluorescence                | Yes     | Yes    | Yes              | Yes | Yes               |
| Scintillation               | No      | No     | No               | No  | No                |
| Recover @RT                 | Slow    | Slow   | No               | Yes | Yes               |
| <b>Dose Rate Dependence</b> | No      | No     | No               | Yes | Yes               |
| Thermal Annealing           | No/Yes  | No/Yes | Yes              | Yes | Yes               |
| Optical Bleaching           | No/Yes  | No/Yes | Yes              | Yes | Yes               |



# Radiation Induced Absorption




Measured with Hitachi U-3210 Photospectrometer

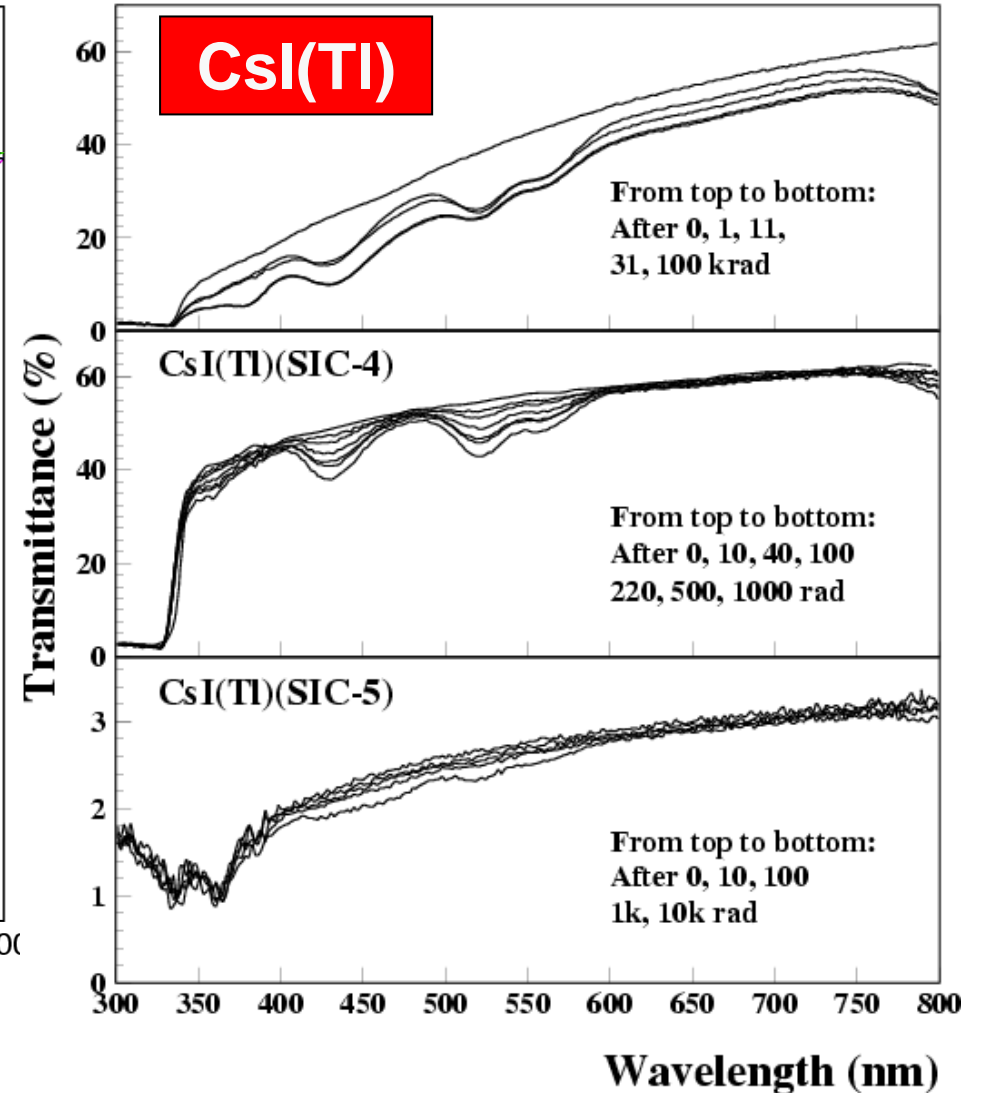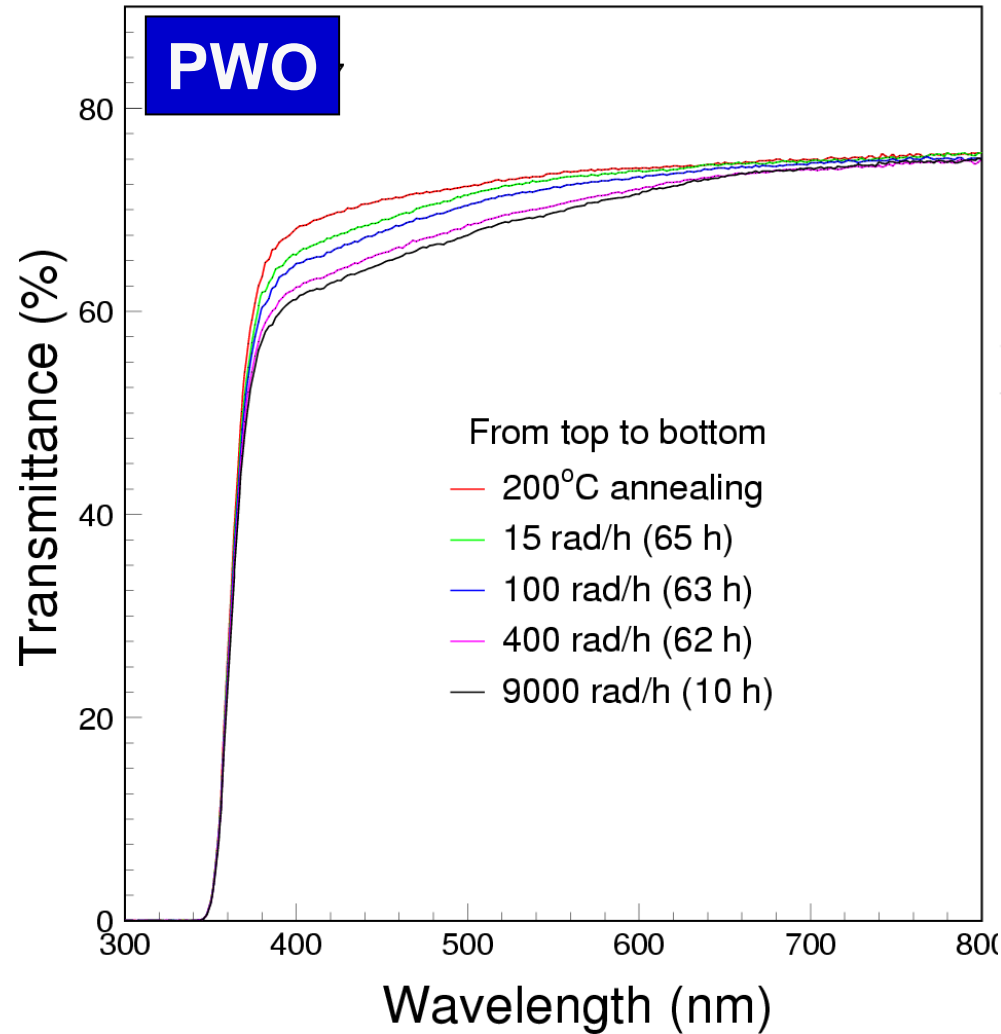



# Dose Rate Dependence




IEEE Trans. Nucl. Sci., Vol. 44 (1997) 468-476

$$dD = \sum_{i=1}^n \{-a_i D_i dt + (D_i^{all} - D_i) b_i R dt\}$$

$$D = \sum_{i=1}^n \left\{ \frac{b_i R D_i^{all}}{a_i + b_i R} [1 - e^{-(a_i + b_i R)t}] + D_i^0 e^{-(a_i + b_i R)t} \right\}$$


- $D_i$ : color center density in units of  $m^{-1}$ ;
- $D_i^0$ : initial color center density;
- $D_i^{all}$  is the total density of trap related to the color center in the crystal;
- $a_i$ : recovery constant in units of  $hr^{-1}$ ;
- $b_i$ : damage constant in units of  $kRad^{-1}$ ;
- $R$ : the radiation dose rate in units of  $kRad/hr$ .

$$D_{eq} = \sum_{i=1}^n \frac{b_i R D_i^{all}}{a_i + b_i R}$$

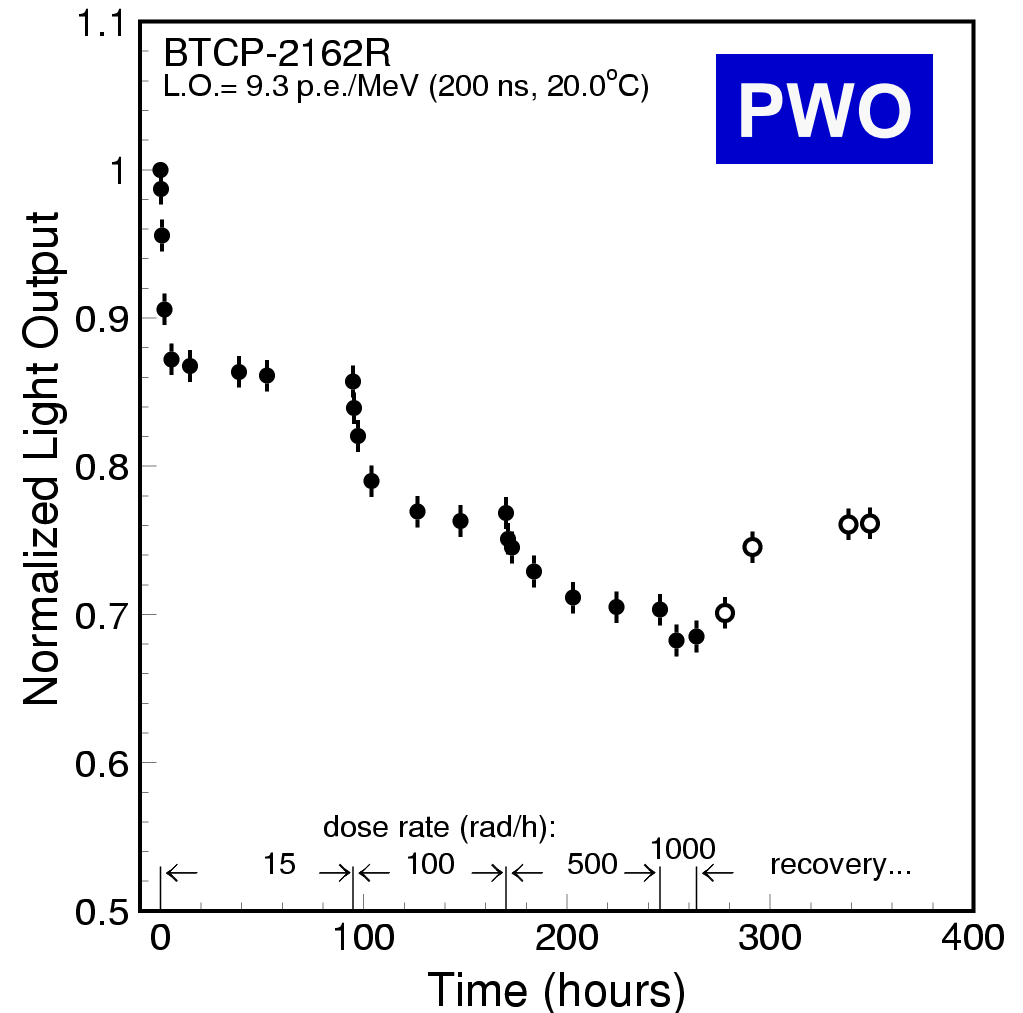





# No Dose Rate Dependence



No/slow recovery: no/less dose rate dependence


**BaF<sub>2</sub>**

**CsI(Tl)**

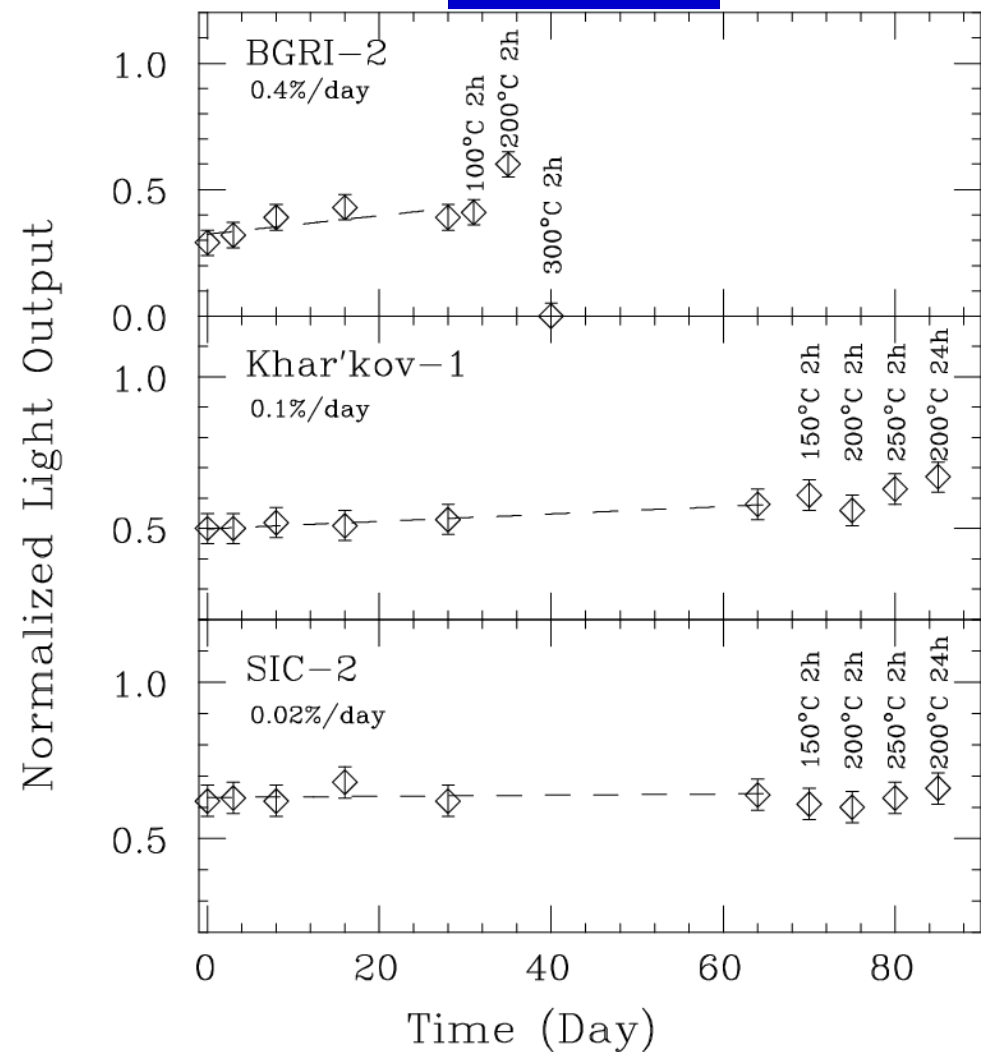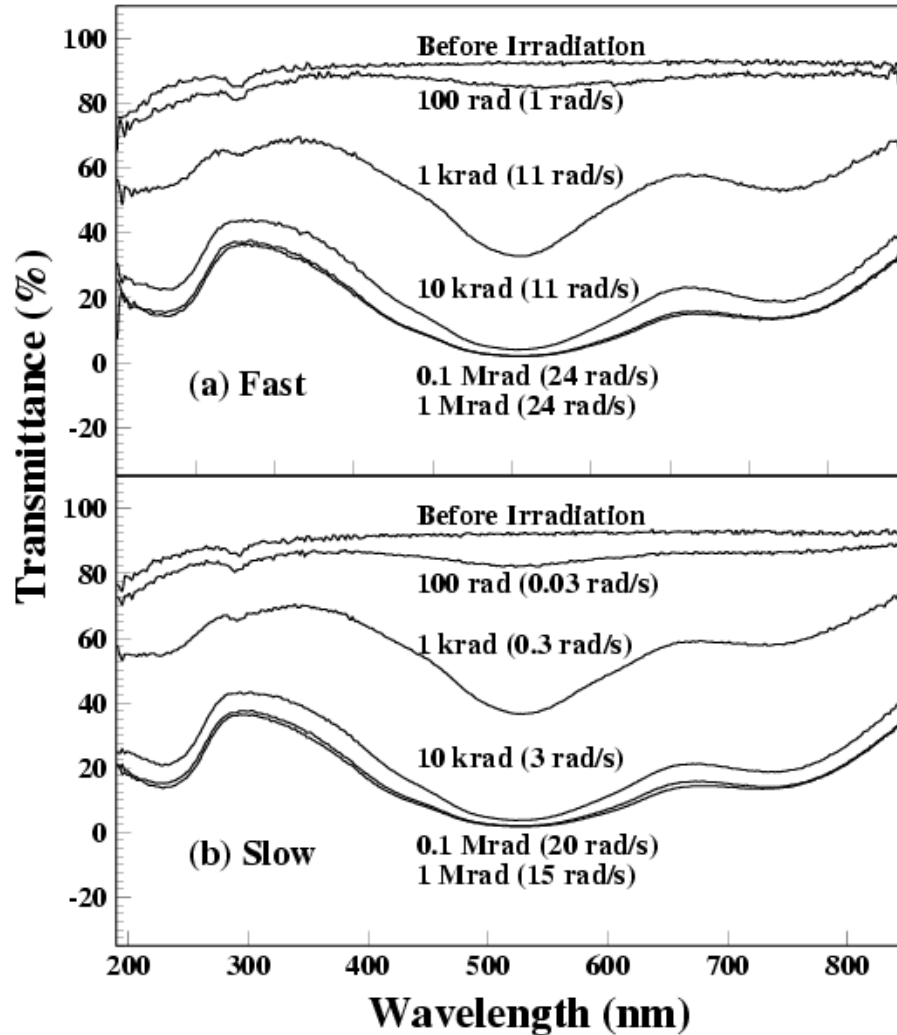




# SIMS Study & CsI(Tl) Improvement




Secondary Ion Mass Spectroscopy revealed depth profile of oxygen contamination; Oxygen control improves CsI(Tl) quality

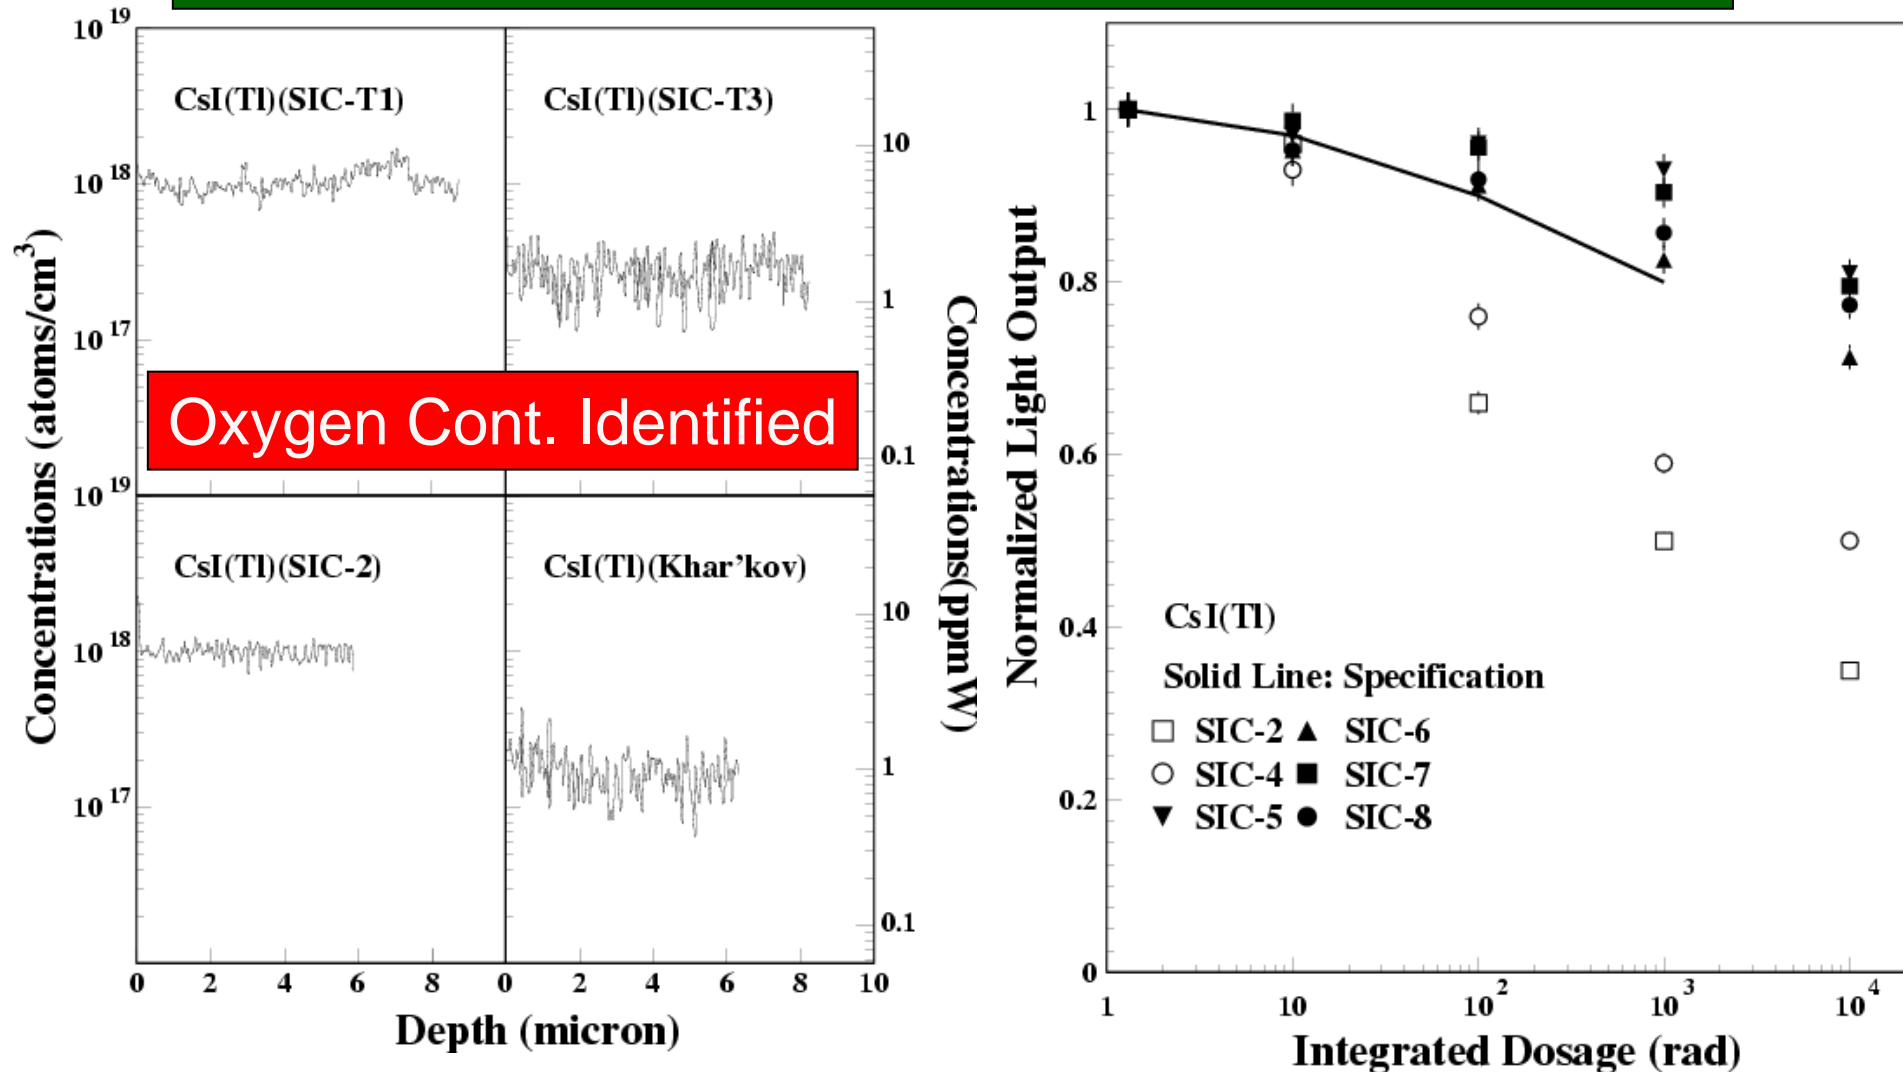




# TEM/EDS Study on PWO Crystals



TOPCON-002B scope, 200 kV, 10 uA, 5 to 10 nm black spots identified  
JEOL JEM-2010 scope and Link ISIS EDS localized Stoichiometry Analysis

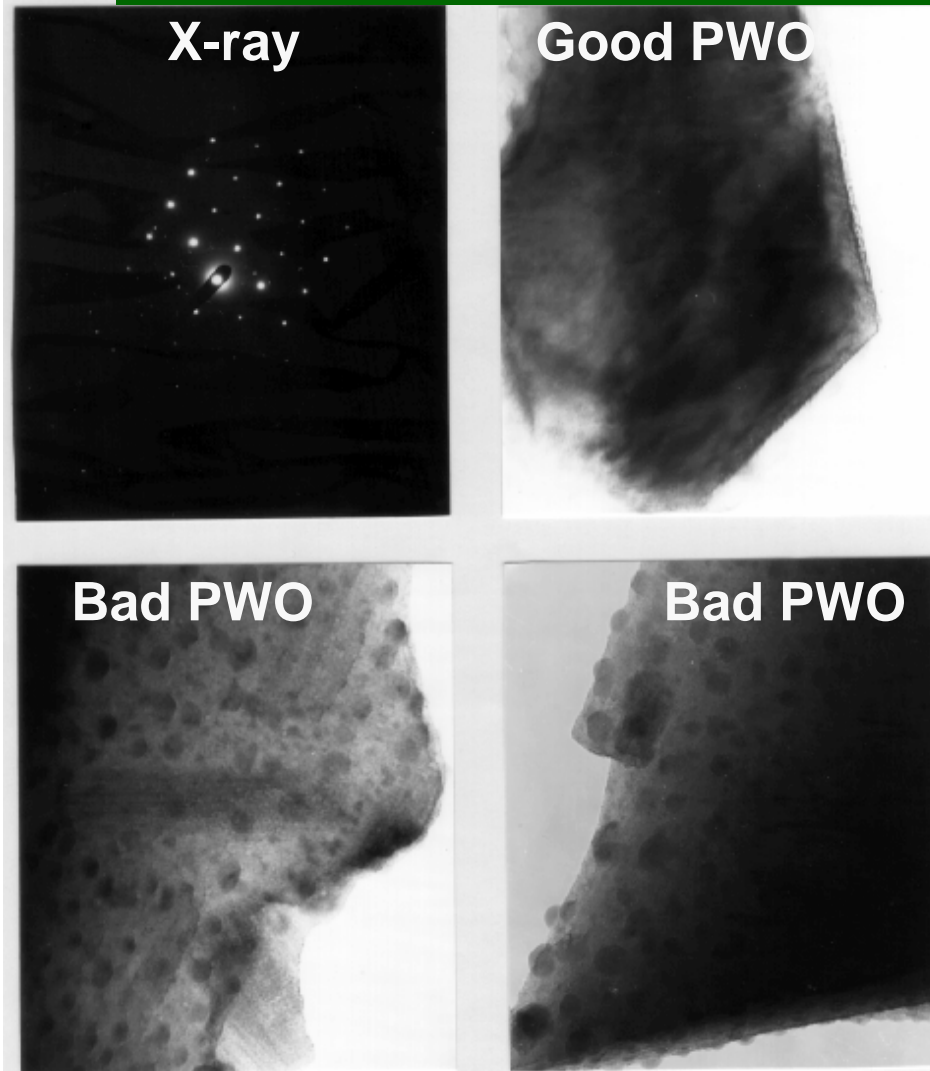

Atomic Fraction (%) in  $PbWO_4$

As Grown Sample

| Element | Black Spot | Peripheral | Matrix <sub>1</sub> | Matrix <sub>2</sub> |
|---------|------------|------------|---------------------|---------------------|
| O       | 1.5        | 15.8       | 60.8                | 63.2                |
| W       | 50.8       | 44.3       | 19.6                | 18.4                |
| Pb      | 47.7       | 39.9       | 19.6                | 18.4                |


The Same Sample after Oxygen Compensation

| Element | Point <sub>1</sub> | Point <sub>2</sub> | Point <sub>3</sub> | Point <sub>4</sub> |
|---------|--------------------|--------------------|--------------------|--------------------|
| O       | 59.0               | 66.4               | 57.4               | 66.7               |
| W       | 21.0               | 16.5               | 21.3               | 16.8               |
| Pb      | 20.0               | 17.1               | 21.3               | 16.5               |

**Oxygen Vacancies Identified**



# BGO/PWO Quality Improvement





Nucl. Instr. and Meth. A302 (1991) 69

Nucl. Instr. and Meth. A480 (2002) 470


BGO damage recovery after 2.5 krad

PWO damage at different dose rate

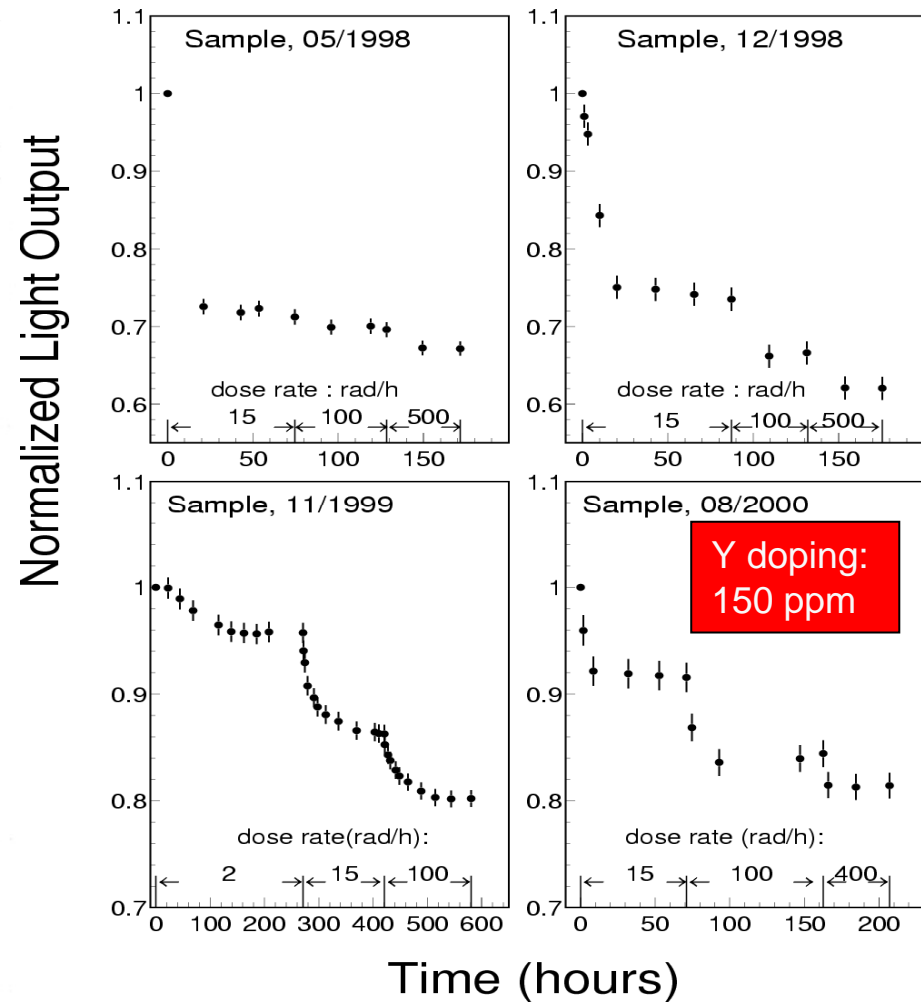
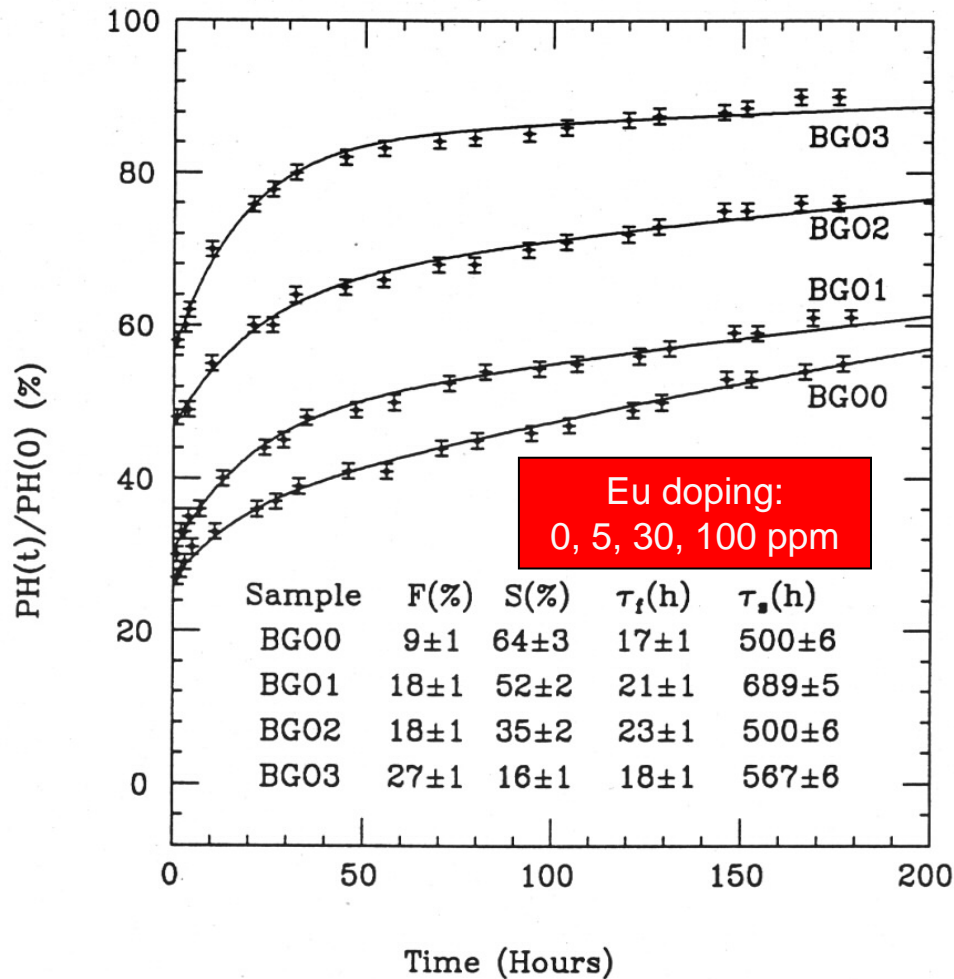




# LYSO Radiation Damage




LT @ 430 nm: 3% increase @ 2 rad/h (19h), 5% degradation @ 9 krad/h (22h)  
Radiation induced phosphorescence: 0.2 & 1 MeV noise @ 15 & 500 rad/h  
IEEE Trans. Nucl. Sci. 52 (2005) 3133

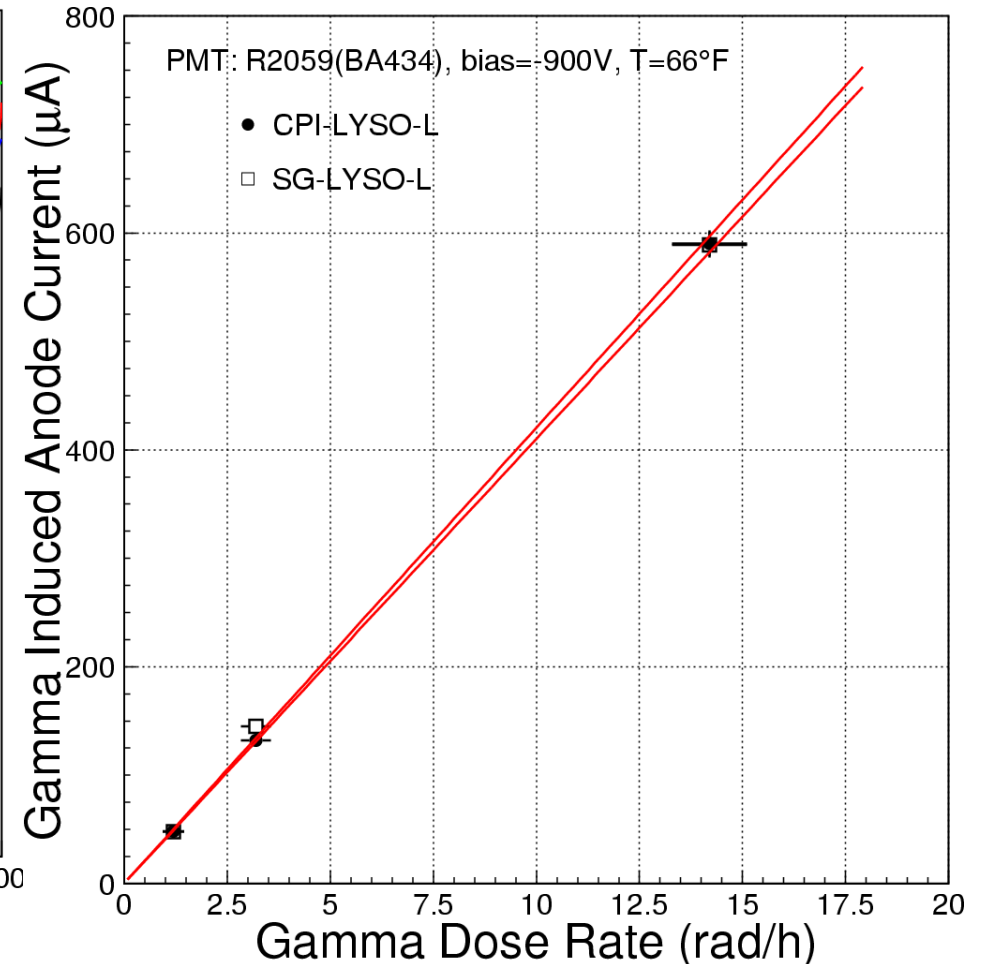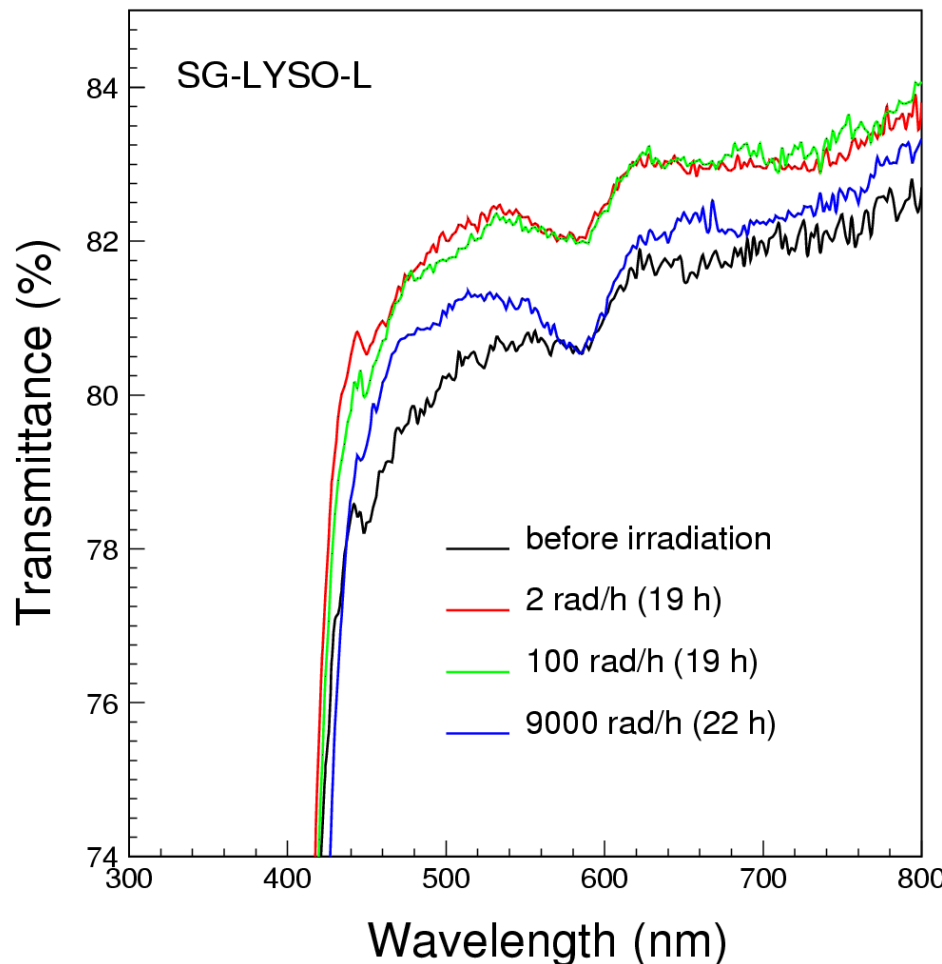





# LSO/LYSO ECAL Performance




- Less demanding to the environment because of small temperature coefficient.
- Radiation damage is less an issue as compared to other crystals.
- A better energy resolution,  $\sigma(E)/E$ , at low energies than L3 BGO and CMS PWO because of its high light output and low readout noise:

$$2.0\% / \sqrt{E} \oplus 0.5\% \oplus .001/E$$




# Summary



- Because of total absorption, precision crystal calorimetry provides the best possible energy and position resolutions for electrons and photons as well as good  $e/\gamma$  identification and reconstruction efficiencies.
- Progress has been made in understanding crystal radiation damage and improving qualities of mass produced crystals.
- An LSO/LYSO crystal calorimeter will provide excellent energy resolution over a large dynamic range down to MeV level for future HEP and NP experiments.



# LAL affects LRU



Nucl. Instr. And Meth. A413 (1998) 297


Ray-Tracing simulation for CMS PWO crystals shows no change in LRU if LAL is longer than 3.5 crystal length

Light collection efficiency, fit to a linear function of distance to the small end of the crystal, was determined with two parameters: the light collection efficiency at the middle of the crystal and the uniformity.

| LAL (cm)  | 20            | 40            | 60           | 80           | 200          |
|---|---------------|---------------|--------------|--------------|--------------|
| Large Area Photo Detector, covering 100% back face  |               |               |              |              |              |
| $\eta_m$ (%)  | $9.5 \pm 2$   | $15.7 \pm 4$  | $19.2 \pm 5$ | $21.6 \pm 6$ | $26.9 \pm 7$ |
| $\delta$ (%)  | $23 \pm 1$    | $-4.6 \pm 8$  | $-11 \pm 1$  | $-15 \pm 1$  | $-15 \pm 1$  |
| $\phi 5$ mm Photo Detector, covering 3.7% back face |               |               |              |              |              |
| $\eta_m$ (%)  | $.38 \pm .04$ | $.74 \pm .08$ | $1.1 \pm .1$ | $1.4 \pm .2$ | $3.0 \pm .3$ |
| $\delta$ (%)  | $23 \pm 4$    | $-3.5 \pm 4$  | $-12 \pm 4$  | $-16 \pm 4$  | $-17 \pm 3$  |
| $\frac{\eta_m(\phi 5mm)}{\eta_m(Full)}$ (%)         | 4.0           | 4.7           | 5.7          | 6.5          | 11           |



# PWO Radiation Damage



No damage in scintillation mechanism  
No damage in resolution if light attenuation length  $> 1$  m

